

EXPLORING WOOD POLYMER COMPOSITES: A SYSTEMATIC VISUAL REVIEW OF COMPOSITION, PRODUCTION, AND PROPERTIES

EXPLORANDO COMPÓSITOS MADEIRA-POLÍMERO: UMA REVISÃO SISTEMÁTICA VISUAL SOBRE COMPOSIÇÃO, PROCESSOS DE PRODUÇÃO E PROPRIEDADES

EXPLORANDO LOS COMPUESTOS DE MADERA Y POLÍMERO: UNA REVISIÓN SISTEMÁTICA VISUAL DE LA COMPOSICIÓN, PRODUCCIÓN Y PROPIEDADES

ANDERSON RAVIK DOS SANTOS, MSc. | UFOP – Universidade Federal de Ouro Preto, Brasil

TIAGO VIEIRA DA SILVA | UFOP – Universidade Federal de Ouro Preto, Brasil

ROMÁRIO PARREIRA PITA, MSc. | UFOP – Universidade Federal de Ouro Preto, Brasil

RIVELINO NERI SILVA, MSc. | UFOP – Universidade Federal de Ouro Preto, Brasil

WANNA CARVALHO FONTES, Dra. | UFOP – Universidade Federal de Ouro Preto, Brasil

ABSTRACT

This systematic review investigates recent advances in wood polymer composites (WPCs), focusing on their composition, processing methods, and physical-mechanical performance for potential structural and sustainable construction applications. Using the adapted Systematic Search Flow methodology, the study analyzed the composition, manufacturing strategies, and physical-mechanical performance of 283 distinct WPC formulations reported in 134 research articles. Extrusion, whether applied independently or in combination with other techniques, emerged as the dominant process for thermoplastic-based WPCs, enabling continuous production and high throughput. Polypropylene (PP) and high-density polyethylene (HDPE) were the most common matrices, typically reinforced with lignocellulosic fillers that enhance stiffness and strength, although often at the cost of increased water absorption, a drawback effectively mitigated by compatibilizing agents. Statistical analyses of tensile, flexural, and water absorption data, presented through detailed graphical representations, serve as a key strength of this work, functioning as powerful visual tools to highlight trends, compare formulations, and facilitate the interpretation of results. The review underscores the versatility of WPCs in addressing environmental challenges such as plastic waste and deforestation, while also highlighting critical gaps in long-term durability, the effects of recycling cycles, and the harmonization of performance benchmarks in international standards. The study concludes that WPCs, when optimally formulated and processed, offer high potential for applications such as decking, facade panels, and modular structural elements, and that aligning future developments with sustainability principles and global standardization will be key to expanding their adoption in engineering and construction sectors.

KEYWORDS

Wood Polymer Composites; Physico-mechanical properties; Production Processes; Sustainability.

RESUMO

Esta revisão sistemática apresenta os avanços recentes em compósitos madeira-polímero (Wood Polymer Composites - WPCs), com ênfase em sua composição, métodos de processamento e desempenho físico-mecânico, visando aplicações estruturais e sustentáveis na construção civil. A partir da metodologia Systematic Search Flow adaptada, foram analisadas 283 formulações distintas de WPCs descritas em 134 artigos científicos. A extrusão, utilizada de forma isolada ou combinada



com outras técnicas, destacou-se como o principal processo de produção para compósitos termoplásticos, viabilizando manufatura contínua e em larga escala. Entre as matrizes mais empregadas, o polipropileno (PP) e o polietileno de alta densidade (PEAD) foram predominantes, geralmente reforçados com cargas lignocelulósicas, que aumentam rigidez e resistência, ainda que elevem a absorção de água, aspecto frequentemente minimizado pelo uso de agentes compatibilizantes. A análise estatística de dados de tração, flexão e absorção de água, organizada em representações gráficas detalhadas, constitui um dos pontos fortes desta revisão, funcionando como ferramenta visual eficaz para destacar tendências, comparar formulações e interpretar resultados. Os achados evidenciam a versatilidade dos WPCs no enfrentamento de desafios ambientais, como o acúmulo de resíduos plásticos e o desmatamento. Contudo, permanecem lacunas relacionadas à durabilidade em longo prazo, aos efeitos de múltiplos ciclos de reciclagem e à necessidade de harmonização de critérios de desempenho em normas internacionais. Conclui-se que, quando formulados e processados de maneira otimizada, os WPCs apresentam elevado potencial para aplicações como decks, painéis de fachada e elementos estruturais modulares. O alinhamento dos futuros desenvolvimentos aos princípios da sustentabilidade e à padronização global será determinante para ampliar sua adoção nos setores de engenharia e construção.

PALAVRAS-CHAVE

Compósitos madeira-polímero; Propriedades físico-mecânicas; Processos de produção; Sustentabilidade.

RESUMEN

Esta revisión sistemática examina los avances recientes en los compuestos de madera y polímero (Wood Polymer Composites - WPCs), con énfasis en su composición, métodos de procesamiento y desempeño físico-mecánico para posibles aplicaciones estructurales y de construcción sostenible. Mediante la metodología adaptada Systematic Search Flow, el estudio analizó la composición, las estrategias de fabricación y el desempeño físico-mecánico de 283 formulaciones distintas de WPC reportadas en 134 artículos de investigación. La extrusión, empleada de forma independiente o en combinación con otras técnicas, se consolidó como el proceso predominante para los WPC basados en termoplásticos, al permitir producción continua y alta eficiencia. El polipropileno (PP) y el polietileno de alta densidad (PEAD) fueron las matrices más utilizadas, comúnmente reforzadas con cargas lignocelulósicas que mejoran la rigidez y la resistencia, aunque con el inconveniente de un incremento en la absorción de agua, limitación que puede mitigarse de manera efectiva mediante agentes compatibilizantes. Los análisis estadísticos de datos de tracción, flexión y absorción de agua, presentados a través de representaciones gráficas detalladas, constituyen una de las principales fortalezas de este trabajo, al servir como herramientas visuales para destacar tendencias, comparar formulaciones y facilitar la interpretación de resultados. La revisión resalta la versatilidad de los WPC para afrontar desafíos ambientales como los residuos plásticos y la deforestación, al tiempo que señala vacíos críticos relacionados con la durabilidad a largo plazo, los efectos de los ciclos de reciclaje y la armonización de los parámetros de desempeño en normas internacionales. Se concluye que los WPC, cuando son formulados y procesados de manera óptima, poseen un alto potencial para aplicaciones como tarimas, paneles de fachada y elementos estructurales modulares; y que la alineación de futuros desarrollos con los principios de sostenibilidad y la estandarización global será clave para ampliar su adopción en los sectores de la ingeniería y la construcción.

PALABRAS CLAVE

Compuestos de madera y polímero; Propiedades físico-mecânicas; Procesos de producción; Sostenibilidad.

1. INTRODUCTION

The composite structures sector faces numerous challenges and opportunities in a rapidly changing business environment, with increasing global pressures to adopt sustainable practices [1,2]. Investors and consumers are paying closer attention to companies' ESG (Environmental, Social and Governance) practices [3], driving demand for materials and processes that minimize environmental impact and align with the principles of the circular economy.

In this context, Wood Polymer Composites (WPC) emerge as a promising sustainable alternative. They combine a polymeric matrix with a reinforcing filler, generally wood waste, enabling the reuse of polymeric and lignocellulosic residues, thereby reducing environmental liabilities and lessening the demand for natural resources. Beyond their environmental appeal, WPC offers significant technological advantages: the polymeric matrix distributes mechanical stresses and protects the filler

from damage, while the filler enhances the material's strength and stiffness [4,5].

Their resistance to moisture, fungi, pests, and mold makes WPC suitable for external applications where natural wood would be unsuitable [6,7]. Consequently, they find applications in construction elements such as profiles, beams, decks, and panels [8-10], as well as in the automotive industry for components like interior panels and vehicle doors [11]. The performance of these products depends on an integrated design approach that considers both optimal material selection and manufacturing parameters.

Figure 1 presents a chronological overview of investigations into WPC, as detailed in the review by Kieling, Santana, and Dos Santos [12]. While WPC is not a recent technological innovation, the field continues to evolve, with research focusing on expanding applications, incorporating new waste streams, improving production methods, and embedding circular economy practices in manufacturing – efforts that collectively strengthen the benchmarking of these materials.

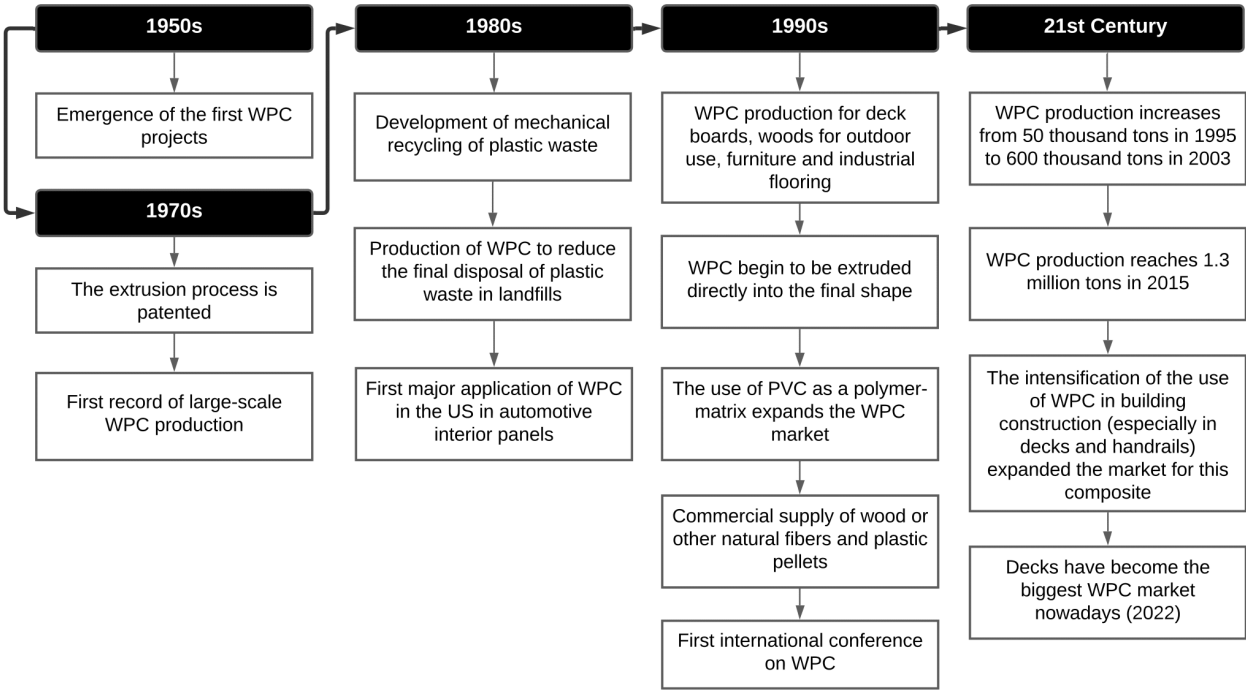


Figure 1: Historical evolution of the Wood Polymer Composite.

Source: The Authors. Adapted from Kieling et al. [12].

Proper WPC design is fundamental to achieving desired performance. This includes selecting appropriate polymers and fillers, often from recyclable sources [11,13,14]. Such a multifaceted approach not only advances material recycling and waste

reduction but also supports several United Nations (UN) Sustainable Development Goals (SDGs), including SDG 12 (Responsible Consumption and Production), SDG 14 (Life Below Water), and SDG 15 (Life on Land). Furthermore, fostering cross-sector collaboration to

develop sustainable solutions such as WPC directly contributes to SDG 17 (Partnerships for the Goals) [2].

The existing literature often addresses WPC through specific lenses, focusing separately on matrices [15], types of fillers [16], production methods [17], compatibilizing agents [18], or material properties [19]. In contrast, this study offers an integrated perspective, employing graphical tools to clarify the complexities involved and conducting in-depth analyses of how these variables influence the physical-mechanical behavior of WPC. By exploring data distributions and identifying outliers, this work provides a comprehensive and updated view that can help expand the structural applications of WPC in strategic industrial sectors.

2. METHODOLOGY

To develop a broad understanding of the characteristics, properties, and processing methods of WPC, a comprehensive literature review was conducted using the adapted Systematic Search Flow (SSF) method [20], which structures the search process to minimize researcher bias. The research protocol (Figure 2) comprised four sequential stages. Searches were performed in Scopus® and Web of Science®, with the most recent search completed in August 2025, using the keywords "wood polymer composite" and *propert** with Boolean operators. The scope was restricted to journal articles published between 2016 and 2023, without language limitations. Newspaper articles, book chapters, and other sources were excluded, as evidence from previous studies suggests they often add complexity without offering substantial contributions [21,22].

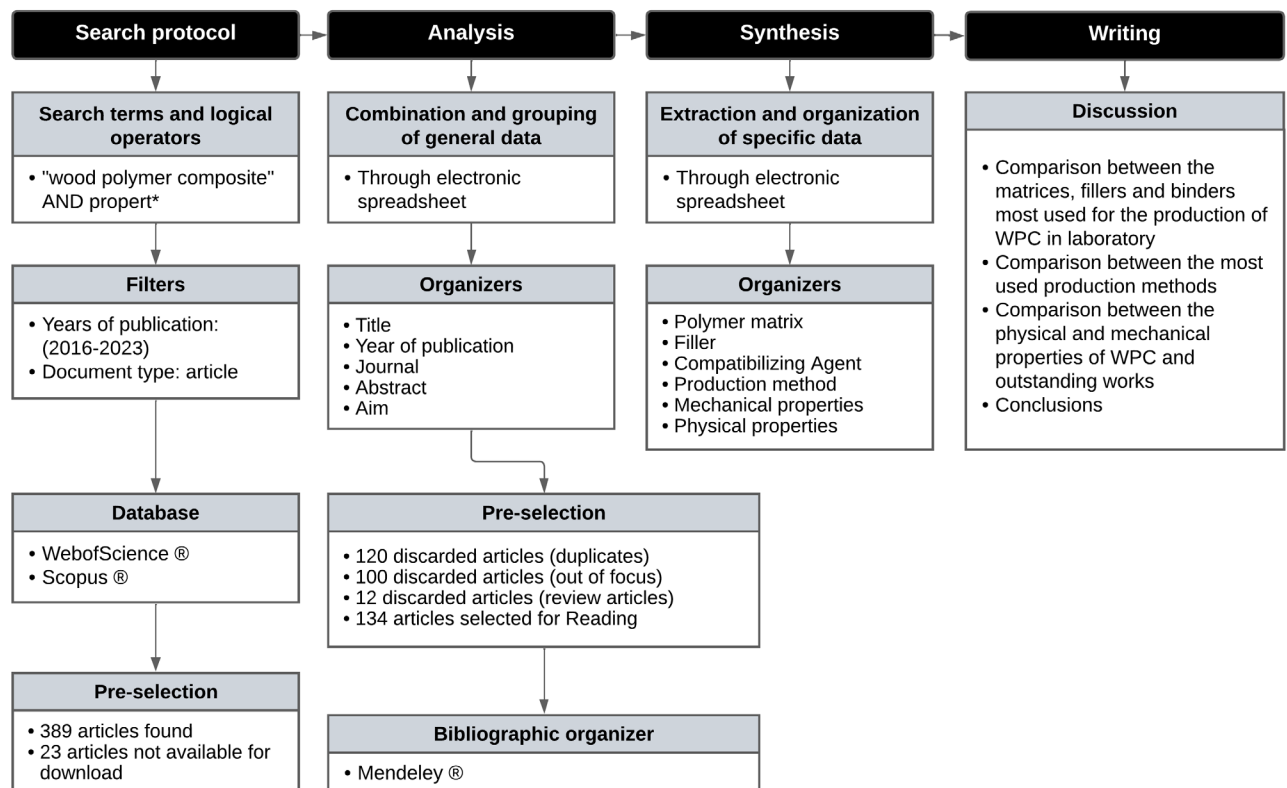


Figure 2: Steps of the literature review process using the adapted SSF method [20].

Source: The Authors.

From the initial 389 records retrieved, 23 were inaccessible and 120 were duplicates, leaving 246 unique articles. Screening excluded 112 papers for being literature reviews or for not addressing WPC materials, processing techniques, or properties. This resulted in a final set of 134 relevant studies. Thus,

the final set comprised only original research articles reporting experimental data on WPC materials, processing, or properties.

Notably, these 134 articles encompassed 283 distinct WPC, since many studies examined multiple composite variations. In this context, a “distinct” WPC

was defined as one differing in the raw materials used or in the production methods, even if reported within the same study. This approach ensured that each variation was evaluated individually, rather than grouping results by article.

3. POLYMERIC MATRICES

The results of the literature review reveal a clear predominance of thermoplastic polymer matrices in the WPC investigated, particularly polypropylene (PP)

(37.8%) and high-density polyethylene (HDPE) (18.4%) [23-39], compared to thermosetting polymers such as polyester (PES), polyurethane (PU), and epoxy resin (ER), which represent less than 2% of the reviewed cases. Thermoplastics are favored for their low cost, ease of processing and recycling due to their ability to be remelted, and chemical resistance from their non-crosslinked polymer chains [40]. Additionally, thermoplastics, especially PP and PE, process at relatively low temperatures (below 200 °C), which helps prevent degradation of wood-based fillers [41,42]. These results are summarized in Figure 3.

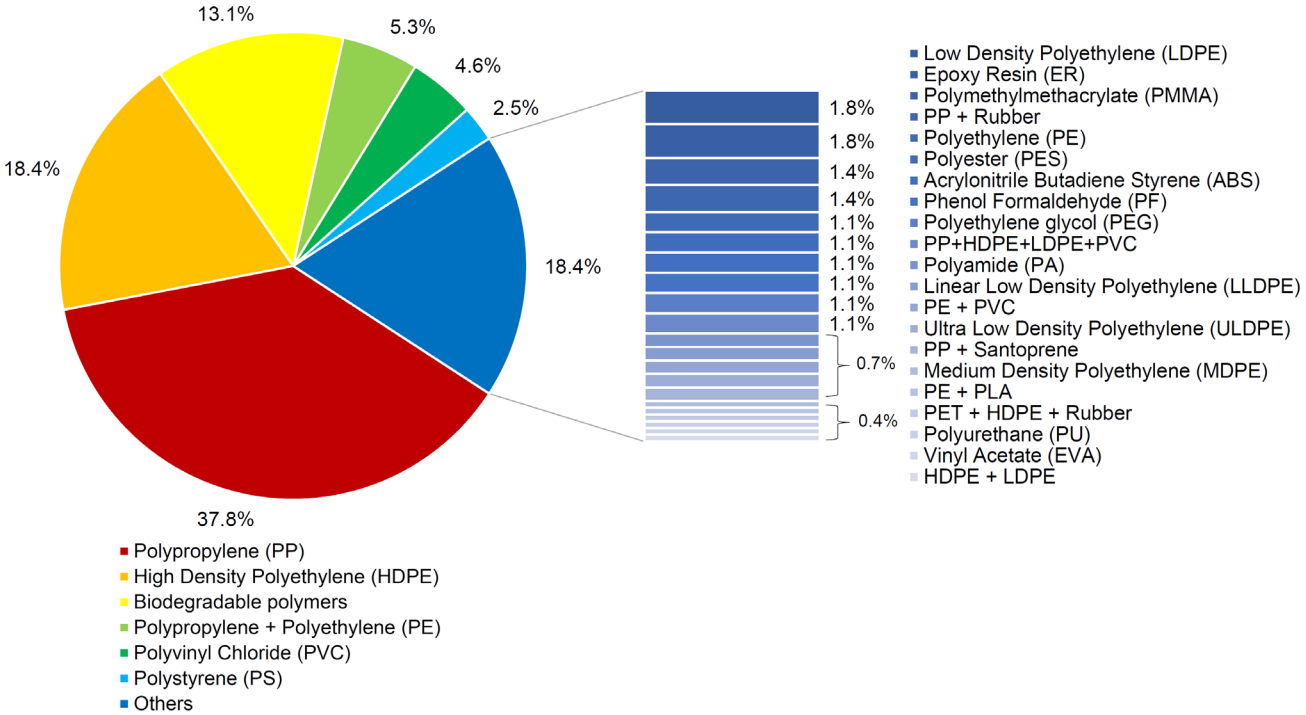


Figure 3: Most used polymers in WPC matrices.
Source: The Authors.

Among thermoplastics, notable matrices also include blends of PP with polyethylene (PE) (5.3%) [43,44], polyvinyl chloride (PVC) (4.6%) [45-48], and polystyrene (PS) (2.5%) [49,50]. PVC offers greater compatibility with lignocellulosic materials due to its hydrophilic molecular structure and the presence of chlorine, which acts as a flame retardant [51]. However, PVC can release dioxins during manufacturing, posing environmental concerns for the WPC industry [41].

Biodegradable polymers represent 13.1% of the identified WPC, enabling the production of fully biodegradable composites when both the filler and the matrix are biodegradable. Examples include polylactic

acid (PLA) [52-54], poly(butylene succinate) (PBS) [55], polycaprolactone (PCL) [56], and modified starches [57]. Growing concerns over pollution caused by commodity plastics have driven a shift toward biodegradable alternatives. Bio-based plastics derived from biomass, when combined with renewable fillers and circular raw resources such as wood, have the potential to further boost the WPC industry. Conventional WPC contribute to microplastic pollution and often end up in landfills, leading to long-term environmental impacts. In contrast, bio-based plastics with high filler content can be relatively low-cost, exhibit excellent mechanical properties, and reduce environmental impact [55].

4. FILLERS

The literature review highlights the predominant use of natural wood particles, either as flour or fibers, as WPC fillers, accounting for 81% of cases, as shown in Figure 4. Incorporating wood fibers into the polymer matrix offers multiple advantages, including lower processing temperatures, reduced molding cycles, lower density, and low abrasiveness [58]. Moreover, wood is a renewable and biodegradable resource, enhancing the sustainability of WPCs [59]. These benefits extend to WPC structural

elements, reinforcing their potential for sustainable construction applications.

Among these composites, 54% use a single wood species as filler, while 5% employ two or more species simultaneously [60-65]. Additionally, 4% of studies explore combining wood with inorganic reinforcements such as chalk [47], glass [66], aramid [67], and printed circuit boards [68]. Other fillers include fiber or particle panels (4%), microcrystalline cellulose (2%) [55], and reprocessed WPC particles (1%) [69].

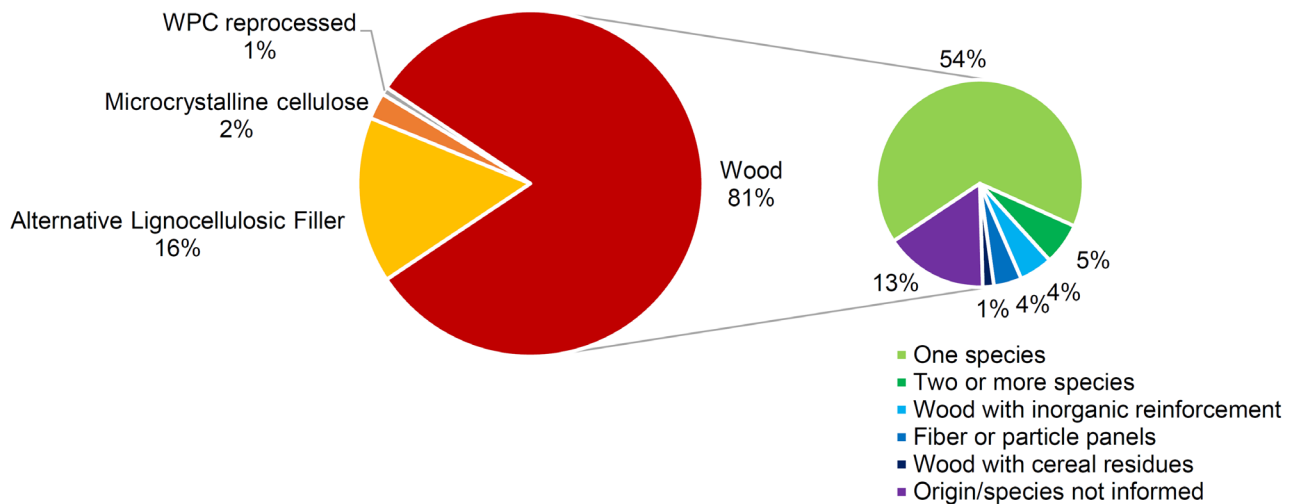


Figure 4: Types of fillers most used in WPC.

Source: The Authors.

Alternative lignocellulosic fillers represent 16% of WPC compositions and include grasses, cereal residues, and fruit byproducts. Examples are bamboo [70, 71], brown coals [72], rice husk [73, 74], rapeseed straw [75], tangerine peel [76], oat husk [77], wheat bran [78], sunflower husk [79], corn straw and cob [80, 81], palm leaves [82], olive pits [83], coffee husks [84], among others. Some studies investigate mixed fillers combining wood and cereal residues, such as coffee husks with brewery grains [85] or coconut shell [86]. Notably, 13% of WPC with wood fillers do not specify the species or origin of the wood [87].

Among those specifying wood species, the most common are Pine (27.0%), Poplar and Fir (16.7% each) and Beech (15.5%) as presented in Figure 5 [23, 68, 88-97]. Less frequently used species (24.1%) include Neem, Flamboyant, Eucalyptus, Birch, Teak, Willow, Sal Tree and Oak, among others [35, 60, 62, 98-103], as well as fruit trees such as Olive [104], Black Cherry [105], and Jackfruit [106].

It is important to note that all natural wood fillers

contain cellulose, hemicellulose, and lignin. Cellulose enhances certain mechanical properties of WPC, such as reduced thermal expansion/ contraction. Lignin, however, can weaken WPC by reducing density and accelerating discoloration upon outdoor exposure. Hemicellulose is susceptible to decomposition at the polymer matrix's melting temperature, producing acetic acid that can severely corrode processing equipment [107]. Understanding these components is essential for optimizing the behavior and properties of natural fiber-reinforced composites, particularly for structural applications.

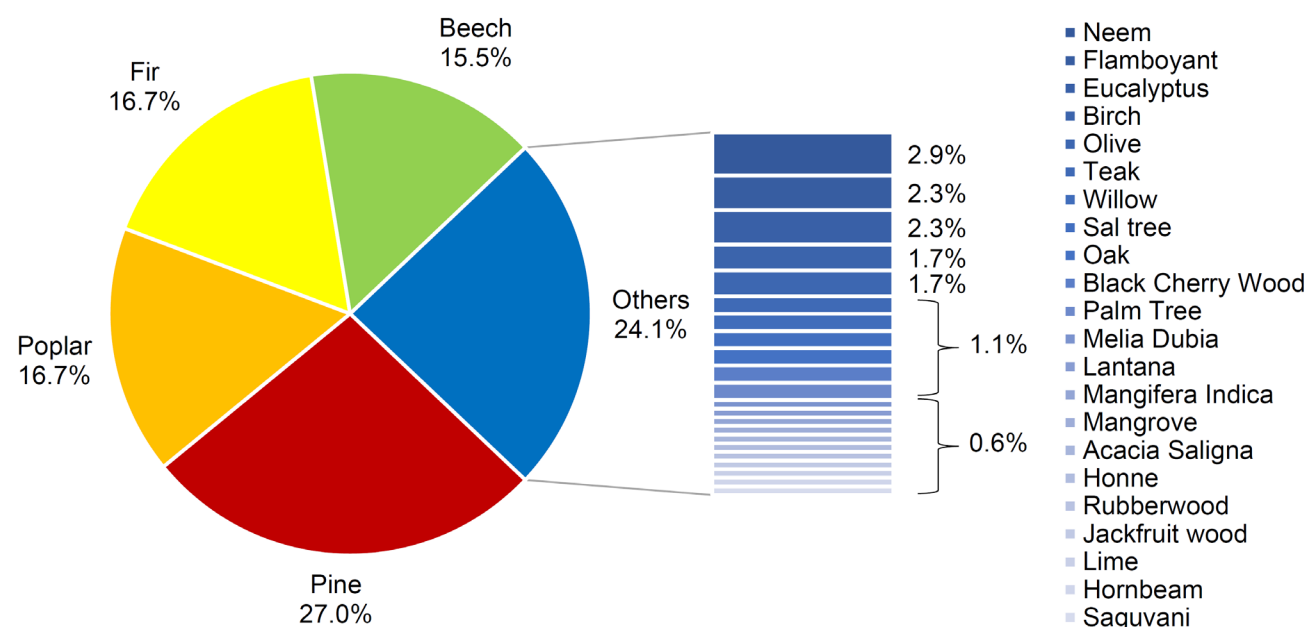


Figure 5: Tree species most used as wood filler.
Source: The Authors.

5. COMPATIBILIZING AGENTS

Although wood and other lignocellulosic fillers are widely used in WPCs, their hydrophilic nature can cause incompatibility with hydrophobic polymer matrices, hindering interfacial adhesion and reducing load transfer efficiency [108]. To address this issue, compatibilizing agents are incorporated in 64.3% of the analyzed cases (Figure 6), acting as chemical intermediaries that enhance matrix-filler interaction, resulting in more homogeneous and stable composites [109]. Maleic anhydride (MA) is the most commonly used agent either in pure form (7.1%) [24,110,111] or grafted onto PP (MAPP)

(5.3%) [57,104,112-114] and PE (MAPE) (4.6%) [115-119]. Its mechanism involves reacting with hydroxyl groups in wood fibers, creating chemical bonds or stronger interactions with the polymer, thereby reducing defects such as porosity and micro-voids [120]. In some cases, adding up to 4 wt% MAPP can increase the flexural modulus of rupture and modulus of elasticity by up to 12.7% and 39.1%, respectively, in composites based on PP, rubber, and rubberwood sawdust [112]. However, not all compatibilizers yield improvements, for instance, ethylene-1-butene weakened the strength of PP composites containing ground tire rubber and pine flour [121].

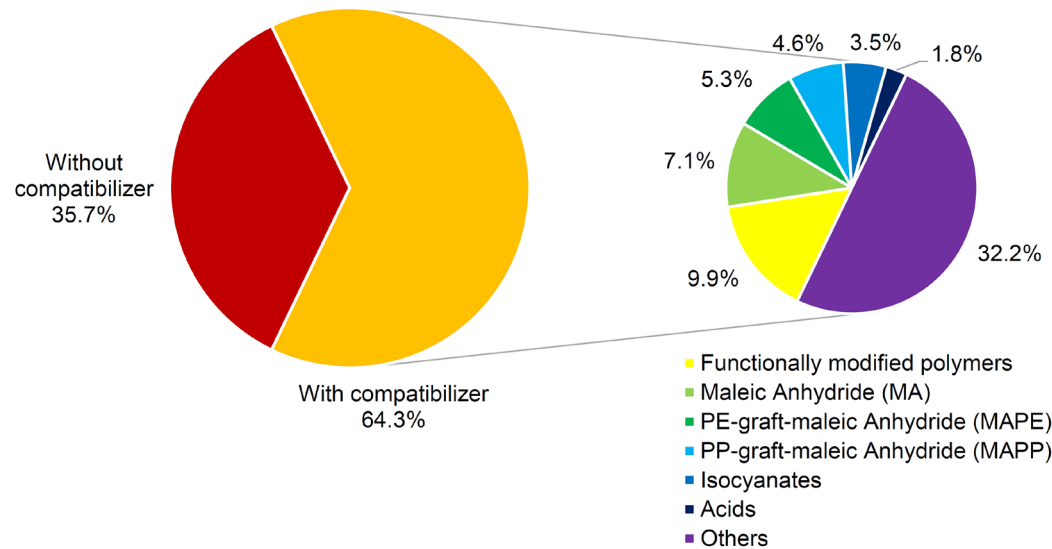


Figure 6: Compatibilizing agents used in the production of WPC.
Source: The Authors.

Despite these benefits, 35.7% of WPCs are produced without compatibilizers [88,122-125], offering simpler formulations and lower costs, although potentially at the expense of mechanical and thermal performance. Beyond MA, MAPP and MAPE, alternative compatibilizers are also employed, such as functionally modified polymers (9.9%) [44,94] and isocyanates (3.5%) [55,56]. Functionally modified polymers incorporate specific groups that enhance adhesion, wettability, or reactivity [126-128], while isocyanates improve phase compatibility to levels equal to or exceeding those of anhydrides [56]. However, due to their toxicity, isocyanates must be used cautiously, with environmental and safety considerations being essential for the development of more sustainable WPCs [18].

6. PROCESSING METHODS

Extrusion is the predominant WPC processing method, used in 39.9% of studies (Figure 7) [30, 32,44,80,129-134]. It ensures uniform component mixing, melting and plastifying materials into profiles, boards, or other shapes, promoting strong organic-inorganic adhesion and optimizing composite properties for diverse applications. Compression molding (21.6%) [135-142] and injection molding (13.1%) [31, 100, 143-147] are also relevant. In compression molding, the matrix and filler are pressed in a mold, which is generally heated, while in injection molding, the molten material is injected into a mold [41]. Compression molding is efficient at lab scale but often produces higher porosity than extrusion or injection, which yield denser, less absorbent composites [61].

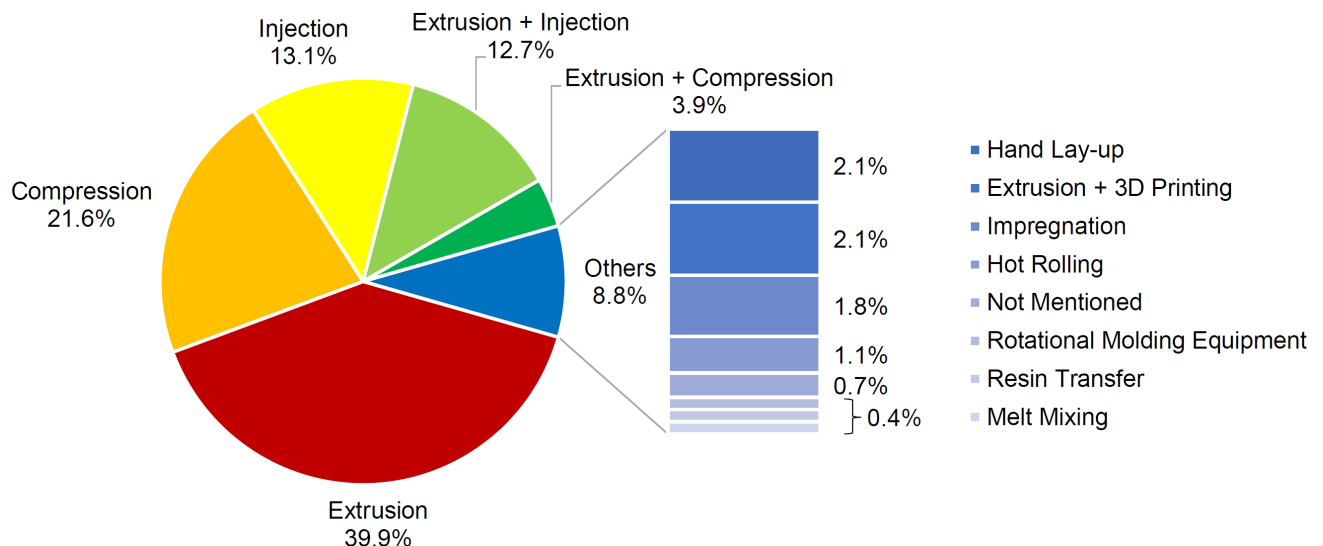


Figure 7: Main processing methods used in research involving WPC.

Source: The Authors.

Hybrid methods combine extrusion with injection (12.7%) [148-150] or compression molding (3.9%) [112,119], where extrusion generally serves as the mixing stage and the subsequent method defines the final geometry and properties [84,96,151,152]. Extrusion can also supply filaments for 3D printing, which are remelted and deposited layer by layer [53,54].

Hand lay-up, despite being labor-intensive, operator-dependent, and less consistent, remains popular for its low cost and versatility [102,103, 153,154]. Fibers are manually arranged and resin applied by hand [155], mainly for thermoset matrices (epoxy, polyester, vinyl ester) [156], whose long curing times enable handling and yield dimensionally stable, chemically, and thermally resistant

composites [157]. Automation has been proposed to improve repeatability [158].

Some studies adopt a structural impregnation approach, modifying entire wood pieces instead of particulate fillers [159]. After delignification to increase porosity while preserving cell walls, polymers such as PMMA [160] or PVA [161] are infiltrated, filling cell lumens without defects and achieving tensile strengths up to 165.3 MPa [160], far above those of conventional WPCs (up to 60 MPa). Other works present prototype processing equipment, such as a rotational molding system with a 360° rotating aluminum mold and oscillating oven for uniform material distribution [162]. In all methods, precise control of temperature, pressure, and speed is critical, as

inadequate conditions cause poor filler dispersion, voids, and reduced mechanical performance [41].

7. MECHANICAL AND PHYSICAL PROPERTIES

Various mechanical and physical properties are evaluated in research involving WPC. Among the mechanical properties, the systematic review showed that tensile and flexural strength tests are the most frequently reported, applied to 75% and 48% of the composites reviewed, respectively. Regarding physical properties, water absorption was the most common, assessed in nearly 30% of the studies, with a 24-hour immersion period adopted in 21% of these cases. Other tests were reported for a smaller subset of composites (less than 30%), including impact strength, shear strength, wear resistance, weathering, color change, viscosity, hardness, and thickness swelling [77,94,95,100,116,144,141].

Statistical analysis of the compiled dataset, summarized in the boxplots of Figure 8, reveals distinct distributions for tensile and flexural strength among the evaluated WPCs. Tensile strength values (n=215) range from 1.56 MPa to 59.20 MPa, with a median of 23.63 MPa and a mean of 24.88 MPa, indicating a relatively symmetric distribution around the central tendency, though with two extreme outliers (152.08 MPa and 255.71 MPa) far exceeding the upper quartile (32 MPa). In contrast, flexural strength (n=135) spans a broader range, from 3.53 MPa to 105.39 MPa, with higher central values, a median of 37 MPa and a mean of 39.29 MPa, and no statistical outliers. Overall, flexural strength not only exhibits higher absolute values compared to tensile strength but also a wider interquartile range (19.50-55.30 MPa vs. 12.58-32 MPa), reflecting its generally higher magnitude in WPCs, since flexural loading induces a combination of tensile and compressive stresses, allowing the material to sustain higher apparent strengths than in pure tension.

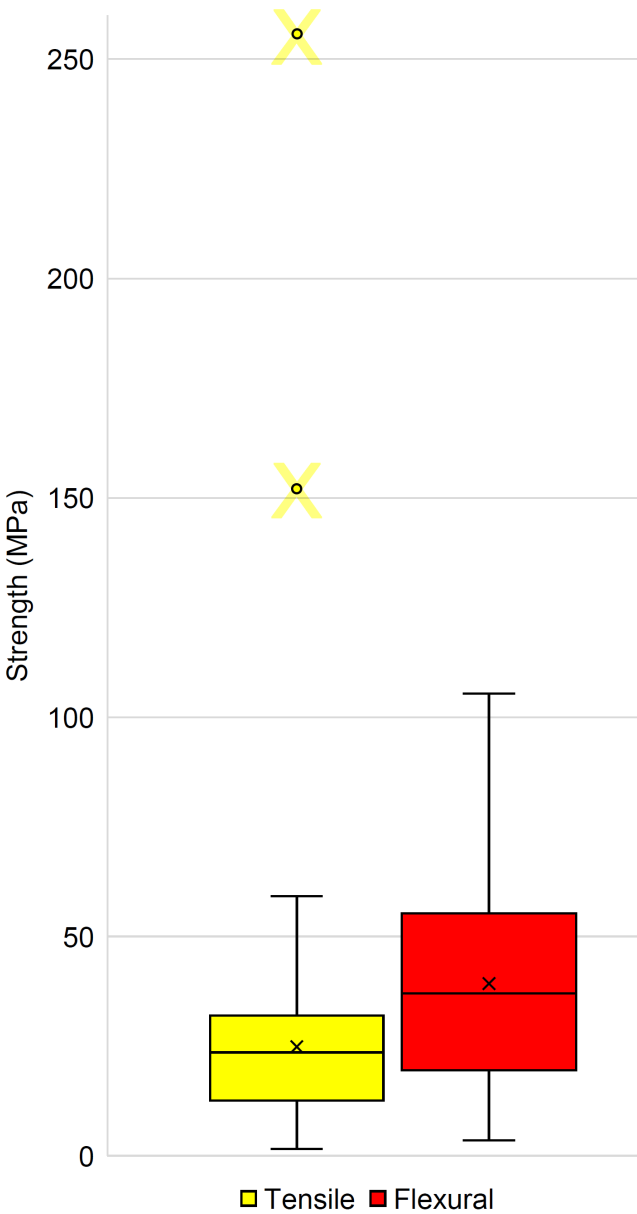


Figure 8: Results of composites subjected to tensile and flexural strength tests.
Source: The Authors.

One of the main challenges in developing WPCs is achieving efficient interfaces between the polymer matrix and lignocellulosic fillers, thereby maximizing stress transfer and, consequently, mechanical properties. For this reason, a large share of studies investigates the effect of compatibilizing agents, especially MA, on mechanical performance, with emphasis on tensile strength. The addition of moderate amounts of MA or MA-functionalized polymers promotes chemical compatibilization, enhancing macromolecular interpenetration, homogeneous particle dispersion, and improved interfacial adhesion [57].

Experimental results confirm this effect. A PP composite reinforced with bamboo fiber containing 3%

MA exhibited a tensile strength of 15.83 MPa, compared to 5.43 MPa for the same material without compatibilizer [70]. Similarly, PP-based WPCs with MA and residual MDF or MDP fillers, produced by extrusion, reached strengths above 42.00 MPa [69,113,130], while PP composites with beech and ionic liquid (47 MPa) [96], and PP with MDP and MA (59.20 MPa, the maximum value within the boxplot limits) [69] also showed high performance.

On the other hand, composites without compatibilizers generally rank among the lowest in tensile strength. Examples include PET, HDPE and rubber with oak (1.56 MPa) [99] and PP with acacia (4.55 MPa) [163], both compression molded; PP with beech (2.89 MPa) and PP with birch (3.16 MPa) by injection molding [100]; and PE with fir by extrusion (4.91 MPa) [93]. Nevertheless, there are notable exceptions: PP and melia dubia WPCs, produced by extrusion and injection, reached 53.70 MPa [152], and PP with fir flour achieved 43.26 MPa [68], even surpassing certain formulations with compatibilizers, such as PP and PE with unspecified wood flour and MA (6.81 MPa) [164], or PP with poplar and azodicarbonamide (6.91 MPa) [43].

The two outliers observed in the boxplot are associated with non-conventional manufacturing processes. In the first case, the process consists of interleaving PVC powder between wood veneers and PVC layers aligned with the fibers, followed by single-step hot molding. This approach promotes cell collapse in the wood and chemical bonding to PVC, producing a dense, interconnected structure with high density and strong bonding, resulting in a mechanical strength of 255.71 MPa, exceeding by over tenfold the average strength of the analyzed WPCs [165]. In the second case, a wood/PMMA composite achieved 165 MPa using delignified linden wood with preserved cellular structure and complete PMMA impregnation, avoiding microstructural defects and leading to outstanding performance [160]. These results reinforce that, while compatibilizers play an important role, careful selection of raw materials and the adoption of innovative manufacturing processes can exert an even greater impact on the mechanical strength of WPCs.

In terms of flexural strength, WPCs produced by extrusion and incorporating compatibilizing agents showed the highest performance. Composites with a PP matrix and MDF or MDP fillers, combined with MA, reached values exceeding 70 MPa [69,113,130]. MDF also stood out in a study assessing the influence of different fillers: three composites, produced with the same matrix (PP), processing method (extrusion followed by compression), and compatibilizer (MAPP), achieved distinct flexural strengths depending on the filler type. The formulation

with MDF (39.31 MPa) outperformed those with hornbeam (37.99 MPa) and pine (31.79 MPa) [166]. The highest flexural strength, 105.39 MPa, was achieved by the same WPC that was an outlier in tensile strength, produced via a single-stage hot molding process using PVC and poplar [165].

Chemically pretreated wood fillers also yielded high flexural strengths, even in composites manufactured by hand lay-up. A WPC reinforced with pine and sal tree, pretreated with silane, reached an average flexural strength of 94 MPa, while a similar composite with alkaline pretreatment achieved 84 MPa [103]. Additionally, a WPC based on epoxidized soybean oil resin, incorporating treated wood flour and MA, recorded 72.49 MPa [138].

At the other end of the spectrum, the lowest flexural strengths were found in a PU-based WPC reinforced with palm leaf fiber and palm oil (3.53 MPa) produced by extrusion [167], and in an epoxy resin-pine composite (5.36 MPa) made by hand lay-up [168]. Similarly, a PES-based WPC with teak and additives for catalysis and curing achieved 6.50 MPa, which increased to 7.11 MPa with the addition of gum resin [102]. These findings highlight the considerable potential of WPCs in flexural applications, particularly for thermoplastic matrices reinforced with chemically pretreated wood fillers.

The mechanical performance of WPCs, as observed in both tensile and flexural tests, is strongly influenced by matrix-filler interactions, filler type, compatibilizers, and processing methods. These same factors also affect physical properties such as water absorption. High filler-matrix adhesion and densely consolidated microstructures, as seen in composites with chemically treated wood or processed via innovative methods, enhance strength while limiting water uptake, mitigating dimensional instability and potential degradation.

Water absorption directly influences the long-term performance of WPCs. Excessive water uptake can cause swelling and deformation of the polymer matrix and wood fibers, weakening interfacial bonds and reducing mechanical properties such as tensile, flexural, and impact strength [169]. Therefore, assessing water absorption is essential for understanding the overall behavior and durability of WPCs.

Statistical analysis of the water absorption values after 24 hours ($n=59$), summarized in the boxplot of Figure 9, shows a markedly skewed distribution. Absorption rates range from 0.17% to 17.5%, with a median of 2.63% and a mean of 6.99%, indicating that most composites exhibit relatively low water uptake, but a subset presents substantially higher values. The interquartile range (0.78-8.0%) reflects considerable variability among the central 50% of the dataset, while

several extreme outliers (19%, 25.83%, 27%, 31.6%, 48.6%, and 51.07%) demonstrate that, in specific formulations, water absorption can be several times greater than the typical range observed. Such dispersion highlights the strong influence of material composition, processing, and fiber-matrix interactions on the hydrophilic behavior of WPCs.

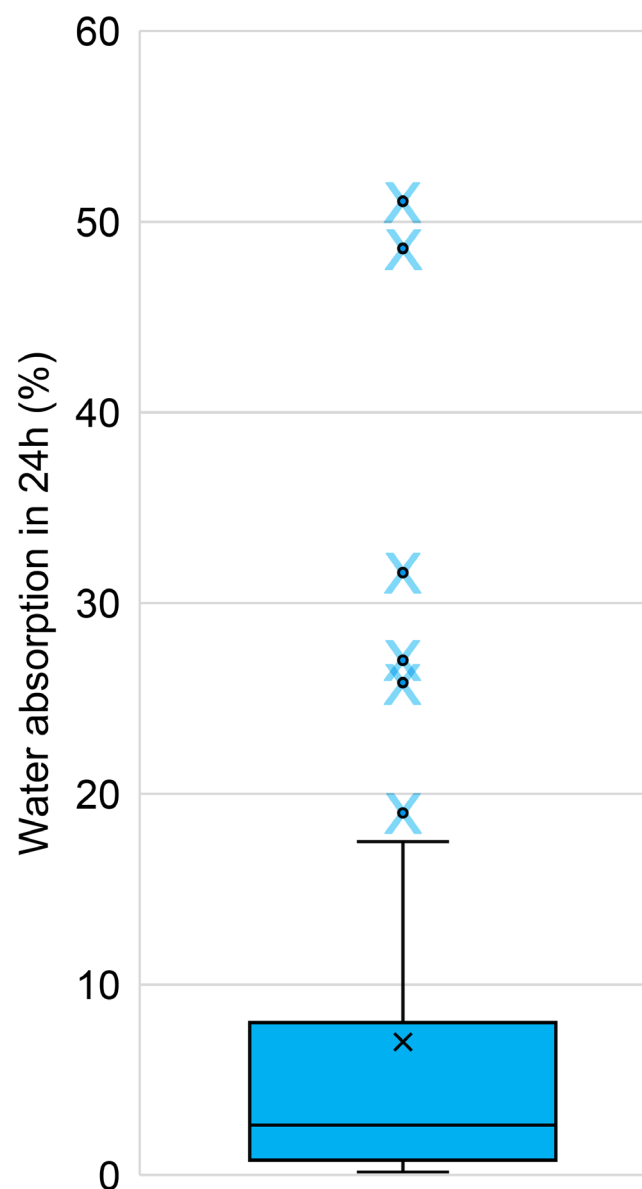


Figure 9: Results of composites subjected to the 24-hour water absorption test.
Source: The Authors.

The water absorption behavior of WPCs varies widely depending on formulation and processing parameters. The lowest mean value reported (0.17%) was obtained for a PVC-based composite with wood flour [47], in a study that extended earlier work where part of the wood filler was replaced with chalk as a mineral filler, combined with dioctyl phthalate plasticizer, to reduce water uptake [48].

Processing route plays a central role in this variability. Although some extruded composites have shown absorption levels below the second quartile (2.63%) [47,77,115], extrusion can adversely affect moisture resistance. A comparative study on composites with identical formulations demonstrated that extruded specimens absorbed more water than those produced by compression or injection molding [170]. The superior performance of injection-molded composites was attributed to the formation of a polymer-rich surface layer under high processing temperatures and pressures, providing a more effective barrier against moisture. Compression molding, however, can surpass injection molding in WPC production due to its lower shear stresses and more controlled temperatures, which better preserve fiber integrity, leading to improved tensile and flexural properties, an effect that can be enhanced through compatibilizer addition [157]. Longer exposure to pressure and heat during compression molding also contributes to reduced water ingress compared to extrusion.

Within compression molding, processing temperature is particularly influential. The most extreme outlier in the boxplot (51.07%) corresponds to a composite based on PS where absorption decreased dramatically as pressing temperature increased, from 51.07% at 413 K (~140 °C) to only 1.33% at 493 K (~220 °C) [49]. This improvement was further supported by filler refinement: composites with sifted sawdust absorbed less water than those with unsifted sawdust, a result attributed to denser packing, lower void volume, and reduced porosity. Additionally, the incorporation of additives such as calcium carbonate (CaCO_3) can further reduce water absorption in WPCs, particularly in composites based on recycled PP. For instance, a formulation containing 70% wood flour and 30% recycled PP showed a reduction in water uptake from 4% to 2% after 24 hours of immersion, which could be further decreased to 1.5% with the addition of 7% CaCO_3 by weight, effectively minimizing the influence of the PP/wood ratio [171].

Composition also plays a decisive role, as illustrated by two other extreme outliers (48.6% and 31.6%), both associated with starch-based WPCs. While starch and other natural polymers are promising for biodegradable composites, their high moisture sensitivity restricts their applicability. Incorporating appropriate fillers has proven to be an effective means of reducing this sensitivity while simultaneously enhancing mechanical performance [57].

Overall, these findings reinforce the interdependence between formulation, processing route, and microstructural development in determining the water absorption

performance of WPCs. Optimizing these parameters – particularly processing temperature, filler characteristics, and molding technique – is essential for achieving composites with low water uptake and robust mechanical properties.

8. FILLER CONTENT

Filler content in polymer composites directly affects their mechanical, physical, and processing properties [130]. Figure 10 summarizes the distribution of filler contents reported in the reviewed studies. The most frequent formulations are concentrated between 20 and 40 wt%, with the 30–40 wt% range showing the highest occurrence, which is consistent with the recommendation of Kieling et al. [12], who suggest the use of up to 40 wt% vegetal fibers in WPCs produced from recyclable materials. Nonetheless, 9.8% of the analyzed formulations contain more than 60 wt% fiber, highlighting the feasibility of achieving higher loadings and, consequently, greater reuse of recycled material as filler. Although the present discussion focuses on fiber content, particle morphology also plays a significant role in composite performance. Fibrous shapes combined with a homogeneous particle-size distribution are generally associated with better dispersion within the matrix and enhanced mechanical properties [172,173].

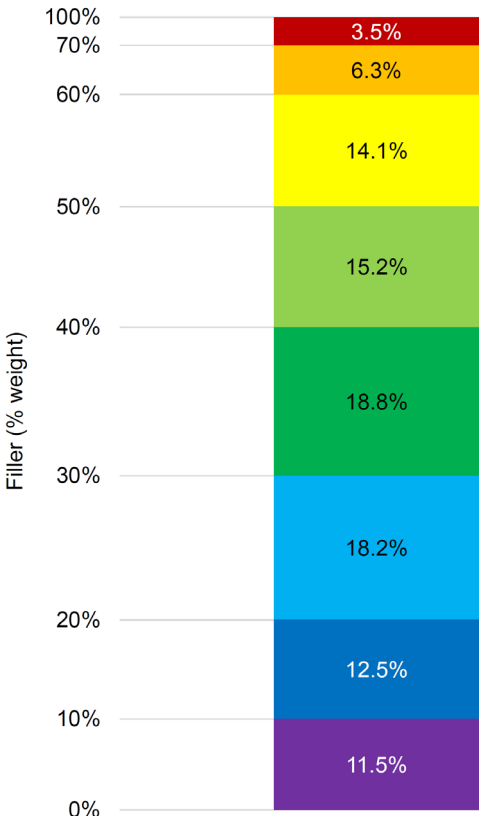


Figure 10: Distribution of filler content (wt%).
Source: The Authors.

In general, increasing filler content tends to reduce the mechanical properties of WPCs, an effect particularly evident in studies that systematically varied this parameter [46,62,76,93,154]. For instance, tensile strength decreased by 31% when coffee silverskin content increased from 2% (22.7 MPa) to 20% (15.6 MPa) [84]. In the same study, replacing the filler with wheat bran resulted in an even greater loss of 47%, from 2.5% (17 MPa) to 20% (9 MPa). These reductions were attributed to increased porosity and insufficient interfacial adhesion, exacerbated by the presence of proteins that may reduce stress transfer by allowing the polymer matrix to slide over the filler particles.

In some cases, an initial increase in tensile strength was observed with increasing filler content, followed by a decline. The initial gain was associated with improved microcellular structure and an increase in the effective load-bearing area, while the subsequent reduction was linked to intensified filler-filler interactions and particle agglomeration [164,167,174]. However, the trend for flexural strength does not always mirror that of tensile behavior. For example, increasing acacia fiber content from 50% to 70% resulted in a 43% decrease in tensile strength (from 23 to 13 MPa) and a 50% decrease in flexural strength (from 6.50 to 3.25 MPa) [163]. Conversely, another study reported only a 5% decrease in tensile strength when filler content increased from 10% to 30%, accompanied by a 30% increase in flexural strength. In this case, the incorporation of wood fibers enhanced the rigidity of the HDPE matrix, which improved its flexural performance despite the slight reduction in tensile strength [123]. Higher filler content, particularly with wood-based composites, also increases water absorption [168,175]. This behavior is attributed to the hydrophilic nature of sawdust, which hydroxyl groups form hydrogen bonds with water, compounded by deficient matrix–filler interfaces, resulting in higher water uptake and weight gain [168].

A common strategy to mitigate mechanical property losses in high-filler composites is the use of compatibilizers. Composites without compatibilizers showed decreased tensile and flexural strength with increasing filler content [114], whereas the addition of 3.5% maleic anhydride (AM) in a PP matrix enabled more effective stress transfer to lantana fibers, enhancing strength at higher loadings. Similar behavior was reported in other studies [79,145]. Moreover, the use of various compatibilizing agents (MAPP, lignin, and nanolignin) has been shown to optimize the performance of PP composites with a high filler content, containing 60% industrial wood residues [176].

Overall, these findings highlight that while high filler content offers environmental benefits by increasing the use of recycled material, it can negatively affect the mechanical and physical properties of WPCs, highlighting the importance of controlling particle morphology and considering the use of compatibilizers to improve performance.

9. CRITICAL REFLECTIONS AND FUTURE PERSPECTIVES

The present review was developed with a specific focus on material composition, processing, and performance trends in WPCs, and therefore did not encompass certain broader aspects that nonetheless merit attention in future research. Among these are long-term performance evaluations under aggressive environmental exposures, such as high humidity, ultraviolet radiation, freeze-thaw cycles, and saline or chemically reactive atmospheres, which are essential to validate the suitability of WPCs for demanding structural and infrastructure applications. Similarly, the effects of multiple recycling and reprocessing cycles on mechanical integrity, filler-matrix bonding, and dimensional stability represent a critical area of investigation in the context of circular economy strategies.

WPCs are increasingly applied in exterior and structural contexts, which necessitates compliance with international standards and guidelines. The most widely recognized specification is the American ASTM D7032 [177], which outlines procedures to establish performance ratings for WPC deck boards, guards, and handrails. Additional ASTM standards provide test methods for mechanical characterization, including ASTM D7264 [178] for flexural properties of polymer matrix composite materials, ASTM D790 [179] for flexural properties of plastics and electrical insulating materials, and ASTM D638 [180] for tensile properties of plastics, which may be applied to WPCs. Notably, these standards define how tests should be conducted but do not prescribe fixed benchmark values, as mechanical performance depends on variables such as wood species, polymer type, and manufacturing process. This lack of predefined performance thresholds creates a gap that hinders direct comparison between studies and complicates global standardization efforts for WPC products. Beyond ASTM, the ISO 20819-1 standard [181] specifies requirements for recycled composites, including health and safety considerations, test methods, and procedures to calculate recycled material

content, thereby promoting sustainable production and responsible material sourcing in WPC manufacturing.

From an industrial and regulatory perspective, aligning future research with the requirements of international technical standards, while addressing the absence of harmonized performance benchmarks, will be crucial to enable fair comparisons, facilitate market acceptance, and support the wider adoption of WPCs. At the same time, developing scalable and resource-efficient production strategies can accelerate the integration of these composites into advanced engineering applications, ensuring not only technical reliability but also environmental and economic sustainability.

10. CONCLUSION

This review highlights the strong potential of WPCs as sustainable materials for civil construction, supported by their competitive mechanical performance, low water absorption, and versatility in composition and processing. The predominance of thermoplastic matrices such as PP and HDPE, often combined with compatibilizing agents and properly processed lignocellulosic fillers, enables performance levels suitable for structural use. However, advancing their adoption requires addressing critical gaps, including long-term durability under aggressive conditions, the influence of recycling cycles on properties, and alignment with international technical standards, which currently prescribe testing methods but lack harmonized benchmark values, hindering comparability and global standardization. Future developments should integrate these regulatory and performance considerations with scalable, resource-efficient manufacturing strategies, enabling applications such as decking systems, facade cladding and modular structural panels in sustainable construction.

REFERENCES

- [1] OECD. OECD Economic Outlook, Interim Report September 2024: Turning the Corner. Paris: OECD Publishing, 2024.
- [2] UNITED NATIONS. **Sustainable development goals**. Available at: <<https://www.un.org/sustainabledevelopment/sustainable-development-goals-retired-link/>>. Accessed on Jun. 14, 2024.

[3] KPMG INTERNATIONAL. Big shifts, small steps: survey of sustainability reporting 2022. Available at: <https://assets.kpmg.com/content/dam/kpmg/dk/pdf/dk-2022/dk-SSR-Report_FINAL_web.pdf>. Accessed on Jun. 14, 2024.

[4] SABA, N.; JAWAID, M.; ALOTHMAN, O. Y.; PARIDAH, M.; HASSAN, A. Recent advances in epoxy resin, natural fiber-reinforced epoxy composites and their applications. **Journal of Reinforced Plastics and Composites**, v. 35, p. 447–470, 2016. DOI: <<https://doi.org/10.1177/0731684415618459>>.

[5] CARDARELLI, F. Encyclopaedia of Scientific Units, Weights, and Measures: Their SI Equivalences and Origins. London; New York: Springer, 2005.

[6] CABRAL, S. C.; SILVA, A. J.; SOARES, E. B.; ARAÚJO, R. F.; MIRANDA, Y. M. S. Comparative characteristics of plastic wood with conventional wood. **Voices dos Vales Scientific Journal**, v. 10, p. 1–20, 2016.

[7] CLEMONS, C. Wood-plastic composites in the United States: the interfacing of two industries. **Forest Products Journal**, v. 52, p. 10–18, 2002.

[8] DOS SANTOS, F. A.; CANTO, L. B.; SILVA, A. L. N.; VISCONTE, L. L. Y.; PACHECO, E. B. A. V. Processing and properties of plastic lumber. In: EVINGÜR, G. A.; PEKCAN, Ö.; ACHILIAS, D. S. (Eds.). Thermosoftening Plastics. **IntechOpen**, 2020. DOI: <<https://doi.org/10.5772/intechopen.82819>>.

[9] MITAL'OVÁ, Z.; MITAL, D.; BERLADIR, K. A concise review of the components and properties of wood-plastic composites. **Polymers**, v. 16, p. 1556, 2024. DOI: <<https://doi.org/10.3390/polym16111556>>.

[10] CARUS, M.; EDER, A.; DAMMER, L.; KORTE, H.; SCHOLZ, L.; ESSEL, R.; BREITMAYER, E.; BARTH, M. Wood-Plastic Composites (WPC) and Natural Fibre Composites (NFC): European and Global Markets 2012 and Future Trends in Automotive and Construction. **Hürth: Nova-Institute**, 2015. Available at: <<https://compositesuk.co.uk/wp-content/uploads/2021/12/WPC-NFC-Market-Study-Short-Version-2015.pdf>>. Accessed on Apr. 15, 2022.

[11] JUBINVILLE, D.; ESMIZADEH, E.; TZOGANAKIS, C.; MEKONNEN, T. Thermo-mechanical recycling of polypropylene for the facile and scalable fabrication of highly loaded wood plastic composites. **Composites Part B: Engineering**, v. 219, p. 108873, 2021. DOI: <<https://doi.org/10.1016/j.compositesb.2021.108873>>.

[12] KIELING, A. C.; SANTANA, G. P.; DOS SANTOS, M. C. Plastic wood composites: general considerations. **Scientia Amazonia**, v. 8, 2019.

[13] CHUN, K. S.; SUBRAMANIAM, V.; YENG, C. M.; MENG, P. M.; RATNAM, C. T.; YEOW, T. K.; HOW, C. K. Wood plastic composites made from post-used polystyrene foam and agricultural waste. **Journal of Thermoplastic Composite Materials**, v. 32, p. 1455–1466, 2019. DOI: <<https://doi.org/10.1177/0892705718799836>>.

[14] BASALP, D.; TIHMINLIOGLU, F.; SOFUOGLU, S. C.; INAL, F.; SOFUOGLU, A. Utilization of municipal plastic and wood waste in industrial manufacturing of wood plastic composites. **Waste Biomass Valor**, v. 11, p. 5419–5430, 2020. DOI: <<https://doi.org/10.1007/s12649-020-00986-7>>.

[15] JUBINVILLE, D.; ESMIZADEH, E.; SAIKRISHNAN, S.; TZOGANAKIS, C.; MEKONNEN, T. A comprehensive review of global production and recycling methods of polyolefin (PO) based products and their post-recycling applications. **Sustainable Materials and Technologies**, v. 25, p. e00188, 2020. DOI: <<https://doi.org/10.1016/j.susmat.2020.e00188>>.

[16] ALPÁR, T.; MARKÓ, G.; KOROKNAI, L. Natural fiber reinforced PLA composites: effect of shape of fiber elements on properties of composites. In: THAKUR, V. K.; THAKUR, M. K.; KESSLER, M. R. (Eds.). **Handbook of Composites from Renewable Materials**. 1st ed. Wiley, 2017, p. 287–312. DOI: <<https://doi.org/10.1002/9781119441632.ch30>>.

[17] FRIEDRICH, D. Thermoplastic moulding of wood-polymer composites (WPC): a review on physical and mechanical behaviour under hot-pressing technique. **Composite Structures**, v. 262, p. 113649, 2021. DOI: <<https://doi.org/10.1016/j.compstruct.2021.113649>>.

[18] HEJNA, A.; PRZYBYSZ-ROMATOWSKA, M.; KOSMELA, P.; ZEDLER, Ł.; KOROL, J.; FORMELA, K.

Recent advances in compatibilization strategies of wood-polymer composites by isocyanates. **Wood Science and Technology**, v. 54, p. 1091–1119, 2020. DOI: <<https://doi.org/10.1007/s00226-020-01203-3>>.

[19] FRIEDRICH, D. Comparative study on artificial and natural weathering of wood-polymer compounds: a comprehensive literature review. **Case Studies in Construction Materials**, v. 9, p. e00196, 2018. DOI: <<https://doi.org/10.1016/j.cscm.2018.e00196>>.

[20] FERENHOF, H. A.; FERNANDES, R. F. Demystifying the literature review as basis for scientific writing: SSF Method. **ACB Journal**, v. 21, p. 550–563, 2016. Available at: <https://revista.acbsc.org.br/racb/article/view/1194/pdf_1>.

[21] WUNI, I. Y.; SHEN, G. Q. P.; OSEI-KYEI, R. Scientometric review of global research trends on green buildings in construction journals from 1992 to 2018. **Energy and Buildings**, v. 190, p. 69–85, 2019. DOI: <<https://doi.org/10.1016/j.enbuild.2019.02.010>>.

[22] HOSSEINI, M. R.; MARTEK, I.; ZAVADSKAS, E. K.; AIBINU, A. A.; ARASHPOUR, M.; CHILESHE, N. Critical evaluation of off-site construction research: A scientometric analysis. **Automation in Construction**, v. 87, p. 235–247, 2018. DOI: <<https://doi.org/10.1016/j.autcon.2017.12.002>>.

[23] GILL, Y. Q.; ABID, U.; IRFAN, M. S.; SAEED, F.; SHAKOOR, A.; FIRDAUS, A. Fabrication, characterization, and machining of polypropylene/wood flour composites. **Arabian Journal for Science and Engineering**, v. 47, n. 8, p. 5973–5983, 2022. DOI: <<https://doi.org/10.1007/s13369-021-05768-4>>.

[24] SHOJAIE, M. H.; HEMMASI, A. H.; TALAEIPOUR, M.; GHASEMI, E. Effect of gamma-ray and melt flow index of polypropylene on the properties of the lignocellulosic composite. **Radiation Physics and Chemistry**, v. 177, p. 109126, 2020. DOI: <<https://doi.org/10.1016/j.radphyschem.2020.109126>>.

[25] BOUHAMED, N.; SOUISSI, S.; MARECHAL, P.; AMAR, M. B.; LENOIR, O.; LEGER, R.; BERGERET, A. Ultrasound evaluation of the mechanical properties as an investigation tool for the wood-polymer composites including olive wood flour. **Mechanics of Materials**,

v. 148, p. 103445, 2020. DOI: <<https://doi.org/10.1016/j.mechmat.2020.103445>>.

[26] MAZZANTI, V.; MALAGUTTI, L.; SANTONI, A.; SBARDELLA, F.; CALZOLARI, A.; SARASINI, F.; MOLLI, F. Correlation between mechanical properties and processing conditions in rubber-toughened wood polymer composites. **Polymers**, v. 12, n. 5, p. 1170, 2020. DOI: <<https://doi.org/10.3390/polym12051170>>.

[27] KALALI, E. N.; ZHANG, L.; SHABESTARI, M. E.; CROYAL, J.; WANG, D.-Y. Flame-retardant wood polymer composites (WPCs) as potential fire safe bio-based materials for building products: Preparation, flammability and mechanical properties. **Fire Safety Journal**, v. 107, p. 210–216, 2019. DOI: <<https://doi.org/10.1016/j.firesaf.2017.11.001>>.

[28] MYSIUKIEWICZ, O.; JABŁOŃSKI, P.; MAJCHROWSKI, R.; ŚLEDZIK, R.; STERZYŃSKI, T. Frictional properties of α -nucleated polypropylene-based composites filled with wood flour. In: GAPIŃSKI, B.; SZOSTAK, M.; IVANOV, V. (Eds.). **Advances in Manufacturing II**. Cham: Springer, 2019. p. 461–472. DOI: <https://doi.org/10.1007/978-3-030-16943-5_39>.

[29] VOLFSON, S. I.; FAYZULLIN, I. Z.; MUSIN, I. N.; FAYZULLIN, A. Z.; GRACHEV, A. N.; PUSHKIN, S. A. The physicomechanical and rheological characteristics of wood-polymer composites based on thermally and mechanically modified filler. **International Polymer Science and Technology**, v. 44, p. 39–43, 2017. DOI: <<https://doi.org/10.1177/0307174X1704400208>>.

[30] KRAUSE, K. C.; MÜLLER, M.; MILITZ, H.; KRAUSE, A. Enhanced water resistance of extruded wood-polypropylene composites based on alternative wood sources. **European Journal of Wood and Wood Products**, v. 75, n. 1, p. 125–134, 2017. DOI: <<https://doi.org/10.1007/s00107-016-1091-5>>.

[31] FRACZ, W.; JANOWSKI, G. Predicting effect of fiber orientation on chosen strength properties of wood-polymer composites. **Composites Theory and Practice**, v. 19, p. 56–63, 2019.

[32] HUANG, R.; ZHANG, X.; ZHOU, C. Mechanical, flammable, and thermal performances of co-extruded wood polymer composites with core-shell structure

containing barite-filled shells. **Wood Science and Technology**, v. 54, n. 5, p. 1299–1318, 2020. DOI: <<https://doi.org/10.1007/s00226-020-01213-1>>.

[33] AL-MAQDASI, Z.; GONG, G.; NYSTRÖM, B.; EMAMI, N.; JOFFE, R. Characterization of wood and graphene nanoplatelets (GNPs) reinforced polymer composites. **Materials**, v. 13, n. 9, p. 2089, 2020. DOI: <<https://doi.org/10.3390/ma13092089>>.

[34] JIANG, J.; MEI, C.; PAN, M.; CAO, J. Improved mechanical properties and hydrophobicity on wood flour reinforced composites: Incorporation of silica/montmorillonite nanoparticles in polymers. **Polymer Composites**, v. 41, n. 4, p. 1090–1099, 2020. DOI: <<https://doi.org/10.1002/pc.25440>>.

[35] BARBOS, J. D. V.; AZEVEDO, J. B.; CARDOSO, P. D. S. M.; FILHO, F. D. C. G.; RÍO, T. G. D. Development and characterization of WPCs produced with high amount of wood residue. **Journal of Materials Research and Technology**, v. 9, n. 5, p. 9684–9690, 2020. DOI: <<https://doi.org/10.1016/j.jmrt.2020.06.073>>.

[36] MOHAMED, M. R.; NAGUIB, H. M.; EL-GHAZAWY, R. A.; SHAKER, N. O.; AMER, A. A.; SOLIMAN, A. M.; KANDIL, U. F. Surface activation of wood plastic composites (WPC) for enhanced adhesion with epoxy coating. **Materials Performance and Characterization**, v. 8, p. 22–40, 2019. DOI: <<https://doi.org/10.1520/MPC20180034>>.

[37] HUANG, R.; ZHANG, X.; TENG, Z.; YAO, F. Properties of core-half wrapped shell structure wood-polymer composites containing glass fiber-reinforced shells. **BioResources**, v. 15, n. 4, p. 9088–9102, 2020. DOI: <<https://doi.org/10.15376/biores.15.4.9088-9102>>.

[38] TURKADZE, T.; GVENTSADZE, D. I.; MUMLADZE, T.; GORGODZE, G.; BOCHOIDZE, I. Characterization of polypropylene composite reinforced on bio-waste from the production of tung oil. **Environmental Research, Engineering and Management**, Vilnius, v. 79, n. 4, p. 29–38, 2023. DOI: <<https://doi.org/10.5755/j01.ere.79.4.33393>>.

[39] BUSCHALSKY, A.; BRISCHKE, C.; KLEIN, K. C.; KILIAN, T.; MILITZ, H. Biological durability of wood–polymer composites—The role of moisture and aging.

Materials, Basel, v. 15, n. 23, p. 8556, 2022. DOI: <<https://doi.org/10.3390/ma15238556>>.

[40] EBEWELE, R.O. **Polymer Science and Technology**. 2. ed. Boca Raton: CRC Press, 2020.

[41] YADAV, S.M.; LUBIS, M.A.R.; SIHAG, K. A Comprehensive Review on Process and Technological Aspects of Wood-Plastic Composites. **JSL**, v. 9, p. 329–356, 2021. DOI: <<https://doi.org/10.23960/jsl29329-356>>.

[42] YAMAJI, F.M.; BONDUELLE, A. Use of sawdust in the production of wood-plastic composites. **Floresta Journal**, v. 34, p. 59–66, 2004. Available at: <<https://revistas.ufpr.br/floresta/article/viewFile/2375/1984>>.

[43] WANG, S.; XUE, P.; JIA, M.; TIAN, J.; ZHANG, R. Effect of polymer blends on the properties of foamed wood-polymer composites. **Materials**, v. 12, n. 12, p. 1971, 2019. DOI: <<https://doi.org/10.3390/ma12121971>>.

[44] MARTIKKA, O.; KÄRKI, T. Promoting recycling of mixed waste polymers in wood-polymer composites using compatibilizers. **Recycling**, v. 4, n. 1, p. 6, 2019. DOI: <<https://doi.org/10.3390/recycling4010006>>.

[45] ABDRAKHMANOVA, L.A.; GALEEV, R.R.; KHANTIMIROV, A.G.; KHOZHIN, V.G. Efficiency of carbon nanostructures in the composition of wood-polymer composites based on polyvinyl chloride. **Nanobuild**, v. 13, p. 150–157, 2021. DOI: <<https://doi.org/10.15828/2075-8545-2021-13-3-150-157>>.

[46] SAMUILOVA, E.O.; PODSHIVALOV, A.V.; FOKINA, M.I.; CHURSINA, V.S.; STRELNKOVA, I.E.; USPENSKAYA, M.V. Tensile properties of wood plastic composites based on plant-filled polyvinyl chloride/poly(3-hydroxybutyrate-co-3-hydroxyhexanoate) matrices. **Agronomy Research**, v. 18, 2020. DOI: <<https://doi.org/10.15159/AR.20.021>>.

[47] MATSEEVICH, T.; ASKADSKII, A.; KONDRASHCHENKO, V. Modification of WPC Materials by Introduction of Dioctyl Phthalate Plasticator. **IOP Conf. Ser.: Mater. Sci. Eng.**, v. 661, p. 012120, 2019. DOI: <<https://doi.org/10.1088/1757-899X/661/1/012120>>.

[48] MATSEEVICH, T.; MATSEEVICH, A.; ASKADSKII, A. Water absorption of wood-polymer composites of

savewood. **E3S Web Conf.**, v. 97, p. 02043, 2019. DOI: <<https://doi.org/10.1051/e3sconf/20199702043>>.

[49] MUKBANIANI, O.; ANELI, J.; TATRISHVILI, T.; MARKARASHVILI, E.; LONDARIDZE, L.; KVINIKADZE, N.; KAKALASHVILI, L. Wood polymer composite based on a styrene and triethoxy (vinylphenethyl) silane. **Chem. Chem. Technol.**, [s.l.], v. 17, p. 35-44, 2023. DOI: <<https://doi.org/10.23939/chcht17.01.035>>.

[50] REDA, L.; MOHAMED, L.; MOUBARAK, D. I. Influence of self adhesion mechanical and physical properties of palm trees fibers-polystyrene composites. **Egyptian Journal of Chemistry**, [s.l.], v. 65, n. 12, p. 599-606, 2022. DOI: <<https://doi.org/10.21608/ejchem.2022.123682.5524>>.

[51] YEH, S.-K. **Polypropylene-Based Wood-Plastic Composites Reinforced With Nanoclay**. 2007. DOI: <<https://doi.org/10.33915/etd.4352>>.

[52] PICKERING, K.L.; EFENDY, M.G.A. Preparation and mechanical properties of novel bio-composite made of dynamically sheet formed discontinuous harakeke and hemp fibre mat reinforced PLA composites for structural applications. *Industrial Crops and Products*, v. 84, p. 139–150, 2016. DOI: <<https://doi.org/10.1016/j.indcrop.2016.02.005>>.

[53] EZZARAA, I.; AYRILMIS, N.; ABOUELMAJD, M.; KUZMAN, M. K.; BAHLAOUI, A.; ARROUB, I.; BELHOUIDEG, S. Numerical modeling based on finite element analysis of 3D-printed wood-poly(lactic acid) composites: a comparison with experimental data. **Forests**, [s.l.], v. 14, n. 1, p. 95, 2023. DOI: <<https://doi.org/10.3390/f14010095>>.

[54] KRAPEŽ TOME, D.; SCHWARZKOPF, M.; REPIČ, R.; ŽIGON, J.; GOSPODARIČ, B.; KARIŽ, M. Effect of thermal modification of wood particles for wood-PLA composites on properties of filaments, 3D-printed parts and injection moulded parts. **European Journal of Wood and Wood Products**, [s.l.], v. 82, n. 2, p. 403-416, 2024. DOI: <<https://doi.org/10.1007/s00107-023-02018-2>>.

[55] GAIDUKOV, S.; PLATNIEKS, O.; GAIDUKOVA, G.; STARKOVA, O.; BARKANE, A.; BELUNS, S.; THAKUR, V. K. Understanding the impact of microcrystalline cellulose

modification on durability and biodegradation of highly loaded biocomposites for woody like materials applications. **Journal of Polymers and the Environment**, [s.l.], v. 30, n. 4, p. 1435-1450, 2022. DOI: <<https://doi.org/10.1007/s10924-021-02291-3>>.

[56] HEJNA, A.; BARCZEWSKI, M.; KOSMELA, P.; MYSIUKIEWICZ, O.; PIASECKI, A.; TERCJAK, A. Compatibility of sustainable Mater-Bi/poly (ε-caprolactone)/cellulose biocomposites as a function of filler modification. **Materials, Basel**, v. 16, n. 20, p. 6814, 2023. DOI: <<https://doi.org/10.3390/ma16206814>>.

[57] TEACĂ, C. A.; SHAHZAD, A.; DUCEAC, I. A.; TANASĂ, F. The re-/up-cycling of wood waste in wood-polymer composites (WPCs) for common applications. **Polymers, Basel**, v. 15, n. 16, p. 3467, 2023. DOI: <<https://doi.org/10.3390/polym15163467>>.

[58] ZHANG, H.; CUI, Y.; ZHANG, Z. Chemical treatment of wood fiber and its reinforced unsaturated polyester composites. **Vinyl Additive Technology**, v. 19, p. 18–24, 2013. DOI: <<https://doi.org/10.1002/vnl.20321>>.

[59] ROWELL, R.M. *Wood Chemistry and Wood Composites*. 1. ed. Boca Raton: CRC Press, 2005.

[60] MANDAL, M.; BARDHAN, P.; MAJI, T.K. Study of UV stability, biodegradability and physical properties of rosin derivative cross-linked wood polymer composites. **International Wood Products Journal**, v. 11, p. 2–11, 2020. DOI: <<https://doi.org/10.1080/20426445.2019.1706136>>.

[61] RATHNAM, V.; KICHU, A.; DUTTA, N.; MAJI, T.K.; DEVI, N. Influence of organically modified nanoclay and TiO₂ nanopowder on the properties of Azadirachta indica wood flour-reinforced high-density polyethylene, low-density polyethylene, polypropylene, and polyvinyl chloride nanocomposite. **Journal of Thermoplastic Composite Materials**, v. 35, p. 1468–1487, 2020. DOI: <<https://doi.org/10.1177/0892705720935968>>.

[62] BARTON-PUDLIK, J.; CZAJA, K. Fast-growing willow (*Salix viminalis*) as a filler in polyethylene composites. **Composites Part B: Engineering**, v. 143, p. 68–74, 2018. DOI: <<https://doi.org/10.1016/j.compositesb.2018.01.031>>.

[63] SOZEN, E.; ZOR, M.; AYDEMIR, D. The Effect of Nano TiO₂ and Nano Boron Nitride on Mechanical, Morphological and Thermal Properties of WF/PP Composites. **Drvna Ind.**, v. 69, p. 13–22, 2018. DOI: <<https://doi.org/10.5552/drind.2018.1724>>.

[64] WANG, S.; XUE, P.; JIA, M.; CHEN, K. Extrusion foaming behavior of wood plastic composites based on PP/POE blends. **Mater. Res. Express**, v. 6, p. 115345, 2019. DOI: <<https://doi.org/10.1088/2053-1591/ab4f0c>>.

[65] NUKALA, S. G.; KONG, I.; KAKARLA, A. B.; PATEL, V. I.; ABUEL-NAGA, H. Simulation of wood polymer composites with finite element analysis. **Polymers, Basel**, v. 15, n. 9, p. 1977, 2023. DOI: <<https://doi.org/10.3390/polym15091977>>.

[66] FAYZULLIN, I.Z.; MUSIN, I.N.; VOLFSON, S.I.; NIKIFOROV, A.A. Glass-Filled Wood-Polymer Composites Based on Polypropylene. **KEM**, v. 816, p. 197–201, 2019. DOI: <<https://doi.org/10.4028/www.scientific.net/KEM.816.197>>.

[67] ZHANG, J.; LI, Y.; XING, D.; WANG, Q.; WANG, H.; KOU BAA, A. Reinforcement of continuous fibers for extruded wood-flour/HDPE composites: Effects of fiber type and amount. **Construction and Building Materials**, v. 228, p. 116718, 2019. DOI: <<https://doi.org/10.1016/j.conbuildmat.2019.116718>>.

[68] TIAM, S.; LUO, Y.; CHEN, J.; HE, H.; CHEN, Y.; LING, Z. A comprehensive study on the accelerated weathering properties of polypropylene—wood composites with non-metallic materials of waste-printed circuit board powders. **Materials**, v. 12, n. 6, p. 876, 2019. DOI: <<https://doi.org/10.3390/ma12060876>>.

[69] KRAUSE, K.; SAUERBIER, P.; KODDENBERG, T.; KRAUSE, A. Utilization of recycled material sources for wood-polypropylene composites: Effect on internal composite structure, particle characteristics and physico-mechanical properties. **Fibers**, v. 6, p. 1-18, 2018. DOI: <<https://doi.org/10.3390/fib6040086>>.

[70] FAJARDO CABRERA DE LIMA, L. D. P.; CHAMORRO RODRÍGUEZ, C. D.; MINA HERNANDEZ, J. H. Use of organic acids in bamboo fiber-reinforced polypropylene composites: Mechanical properties and

interfacial morphology. **Polymers**, v. 13, n. 12, p. 2007, 2021. DOI: <<https://doi.org/10.3390/polym13122007>>.

[71] KUMAR, R.; GUNJAL, J.; CHAUHAN, S. Effect of borax-boric acid and ammonium polyphosphate on flame retardancy of natural fiber polyethylene composites. **Maderas. Ciencia y tecnología**, [s.l.], v. 24, 2022. DOI: <<http://dx.doi.org/10.4067/s0718-221x2022000100434>>.

[72] SZYMAŃSKA, J.; BEDNAREK, W. H.; SZOSTAK, M.; URBANIAK, W.; PAUKSZTA, D. Fundamental studies of isotactic polypropylene composites with brown coals: structure–properties relationship. **Journal of Natural Fibers**, [s.l.], v. 20, n. 1, p. 2190553, 2023. DOI: <<https://doi.org/10.1080/15440478.2023.2190553>>.

[73] ZAINI, A. S. S. M.; RUS, A. Z. M.; RAHMAN, N. A.; JAIS, F. H. M.; FAUZAN, M. Z.; SUFIAN, N. A. Mechanical properties evaluation of extruded wood polymer composites. **AIP Conference Proceedings**, v. 1877, 2017. DOI: <<https://doi.org/10.1063/1.4999884>>.

[74] RABBANI, F. A.; SULAIMAN, M.; TABASUM, F.; YASIN, S.; IQBAL, T.; SHAHBAZ, M.; ...; SALEEL, C. A. Investigation of tribo-mechanical performance of alkali treated rice-husk and polypropylene-random-copolymer based biocomposites. **Heliyon**, [s.l.], v. 9, n. 11, 2023. DOI: <<https://doi.org/10.1016/j.heliyon.2023.e22028>>.

[75] BEDNAREK, W. H.; MAREK, A. A.; STRZEMIECKA, B.; SZYMAŃSKA, J.; KOPER, E.; PAUKSZTA, D. The role of oxidized polyethylene wax in processing and crystallization of isotactic polypropylene in WPC composites. **Iranian Polymer Journal**, [s.l.], v. 31, n. 10, p. 1263-1271, 2022. DOI: <<https://doi.org/10.1007/s13726-022-01071-7>>.

[76] HEJNA, A.; BARCEWSKI, M.; KOSMELA, P.; ANIŚKO, J.; MYSIUKIEWICZ, O.; MARĆ, M. Mandarin peel as an auspicious functional filler for polymer composites. **Macedonian Journal of Chemistry and Chemical Engineering**, v. 40, n. 1, p. 89-106, 2021. DOI: <<https://doi.org/10.20450/mjce.2021.2236>>.

[77] BOCHKOV, I.; VARKALE, M.; ZICANS, J.; FRANCISZCZAK, P.; BLEDZKI, A. K. Polypropylene composites wear resistance properties due to spelt

and oat grain husks short fiber preparation technology. **BALTTRIB**, v. 1, p. 1–6, 2019.

[78] HEJNA, A.; BARCEWSKI, M.; ANDRZEJEWSKI, J.; KOSMELA, P.; PIASECKI, A.; SZOSTAK, M.; KUANG, T. Rotational molding of linear low-density polyethylene composites filled with wheat bran. **Polymers**, v. 12, n. 5, p. 1004, 2020. DOI: <<https://doi.org/10.3390/polym12051004>>.

[79] BARCEWSKI, M.; MATYKIEWICZ, D.; PIASECKI, A.; SZOSTAK, M. Polyethylene green composites modified with post-agricultural waste filler: thermo-mechanical and damping properties. **Composite Interfaces**, v. 25, p. 287–299, 2018. DOI: <<https://doi.org/10.1080/09276440.2018.1399713>>.

[80] CHEN, B.; CAI, D.; LUO, Z.; CHEN, C.; ZHANG, C.; QIN, P.; CAO, H.; TAN, T. Corn cob residual reinforced polyethylene composites considering the biorefinery process and the enhancement of performance. **Journal of Cleaner Production**, v. 198, p. 452–462, 2018. DOI: <<https://doi.org/10.1016/j.jclepro.2018.07.080>>.

[81] WANG, C.; MEI, J.; ZHANG, L. High-added-value biomass-derived composites by chemically coupling post-consumer plastics with agricultural and forestry wastes. **Journal of Cleaner Production**, v. 284, p. 124768, 2021. DOI: <<https://doi.org/10.1016/j.jclepro.2020.124768>>.

[82] ELMUSHYAKHI, A. Parametric characterization of nano-hybrid wood polymer composites using ANOVA and regression analysis. **Structures**, v. 29, p. 652–662, 2021. DOI: <<https://doi.org/10.1016/j.istruc.2020.11.069>>.

[83] GÜMÜŞ, B. E.; YAĞCI, Ö.; ERDOĞAN, D. C.; TAŞDEMİR, M. Dynamical mechanical properties of polypropylene composites filled with olive pit particles. **Journal of Testing and Evaluation**, v. 47, p. 2551–2561, 2019. DOI: <<https://doi.org/10.1520/JTE20180198>>.

[84] HEJNA, A.; BARCEWSKI, M.; KOSMELA, P.; MYSIUKIEWICZ, O.; KUZMIN, A. Coffee silverskin as a multifunctional waste filler for high-density polyethylene green composites. **Journal of Composite Science**, v. 5, n. 2, p. 44, 2021. DOI: <<https://doi.org/10.3390/jcs5020044>>.

[85] HEJNA, A.; KOROL, J.; KOSMELA, P.; KUZMIN, A.; PIASECKI, A.; KULAWIK, A.; CHMIELNICKI, B. By-products from food industry as a promising alternative for the conventional fillers for wood–polymer composites. **Polymers**, v. 13, n. 6, p. 893, 2021. DOI: <<https://doi.org/10.3390/polym13060893>>.

[86] RAMESH, B. T.; RAMESH, R. S.; BONGALE, A. Experimental investigation of thermal behavior of un-treated and chemically treated PF-based wood polymer composite. **Journal of The Institution of Engineers (India): Series C**, [s.l.], v. 104, n. 3, p. 513–520, 2023. DOI: <<https://doi.org/10.1007/s40032-023-00929-w>>.

[87] ASFANDIYAROVA, L. R.; KHAKIMOVA, G. V.; OVSYANNIKOVA, I. V.; MATVEEVA, A. Y. Wood-polymer nano-modified composite materials for construction purposes. **Nanotekhnologii v Stroitel'stve, Moscovo**, v. 15, n. 6, p. 543–551, 2023. DOI: <<https://doi.org/10.15828/2075-8545-2023-15-6-543-551>>.

[88] PEERBOOMS, W.; PICKERING, K. L. Use of recycled pulped chromated copper arsenate-treated wood fibre in polymer composites. **Journal of Composite Science**, v. 2, n. 2, p. 35, 2018. DOI: <<https://doi.org/10.3390/jcs2020035>>.

[89] CHAN, C. M.; VANDI, L.-J.; PRATT, S.; HALLEY, P.; RICHARDSON, D.; WERKER, A.; LAYCOCK, B. Mechanical performance and long-term indoor stability of polyhydroxyalkanoate (PHA)-based wood plastic composites (WPCs) modified by non-reactive additives. **European Polymer Journal**, v. 98, p. 337–346, 2018. DOI: <<https://doi.org/10.1016/j.eurpolymj.2017.11.041>>.

[90] JAUNSLAVIE TIS, J.; SHULGA, G.; OZOLINS, J.; NEIBERTE, B.; VEROVKINS, A.; VITOLINA, S.; SHAKELS, V. The influence of mechanical and mechanochemical activation of hardwood wood waste on biocomposite properties. **KEM**, v. 800, p. 200–204, 2019. DOI: <<https://doi.org/10.4028/www.scientific.net/KEM.800.200>>.

[91] JAUNSLAVIEITS, J. et al. Effect of the acidic treatment of domestic wood residue on biocomposite wettability and moisture sorption properties. **ETR**, v. 1, p. 129, 2017. DOI: <<https://doi.org/10.17770/etr2017vol1.2538>>.

[92] JIANG, J. et al. How does Pickering Emulsion Pre-treatment Influence the Properties of Wood Flour and its Composites with High-Density Polyethylene? **Polymers**, v. 11, p. 1115, 2019. DOI: <<https://doi.org/10.3390/polym11071115>>.

[93] MICHALSKA-POZOGA, I.; WEGRZYK, S.; RYDZKOWSKI, T. Assessment of influence of extrusion method on selected properties of wood-polymer composites using Taguchi method of experiment planning. **Polimery**, v. 62, p. 686–692, 2017. DOI: <<https://dx.doi.org/10.14314/polimery.2017.686>>.

[94] LAHTELA, V.; KÄRKI, T. A Study on the Effect of Construction and Demolition Waste (CDW) Plastic Fractions on the Moisture and Resistance to Indentation of Wood-Polymer Composites (WPC). **J. Compos. Sci.**, v. 5, p. 205, 2021. DOI: <<https://doi.org/10.3390/jcs5080205>>.

[95] AYDEMIR, D. et al. Accelerated weathering and decay resistance of heat-treated wood reinforced polypropylene composites. **Drv. Ind. (Online)**, v. 70, p. 279–285, 2019. DOI: <<https://dx.doi.org/10.5552/drvind.2019.1851>>.

[96] QUITADAMO, A.; MASSARDIER, V.; VALENTE, M. Interactions between PLA, PE and wood flour: effects of compatibilizing agents and ionic liquids. **Holzforschung**, v. 72, p. 691–700, 2018. DOI: <<https://doi.org/10.1515/hf-2017-0149>>.

[97] MAZZANTI, V.; MALAGUTTI, L.; SBARDELLA, F.; MOLLIKA, F. Processing-properties correlation for a rubber toughened wood plastic composite. **Macromolecular Symposia**, [s.l.], v. 405, n. 1, p. 2100259, out. 2022. DOI: <<https://doi.org/10.1002/masy.202100259>>.

[98] RATHNAM, V.; KICHU, A.; DUTTA, N.; MAJI, T. K.; DEVI, N. Influence of organically modified nanoclay and TiO₂ nanopowder on the properties of Azadirachta indica wood flour-reinforced high-density polyethylene, low-density polyethylene, polypropylene, and polyvinyl chloride nanocomposite. **Journal of Thermoplastic Composite Materials**, [s.l.], v. 35, n. 10, p. 1468–1487, 2022. DOI: <<https://doi.org/10.1177/0892705720935968>>.

[99] COSNITA, M.; CAZAN, C.; POP, M. A.; CRISTEA, D. Aging resistance under short time ultraviolet (UV) radiations of polymer wood composites entirely based on wastes. **Environmental Technology & Innovation**, [s.l.], v. 31, p. 103208, 2023. DOI: <<https://doi.org/10.1016/j.eti.2023.103208>>.

[100] STADLMANN, A. et al. Interfacial Adhesion and Mechanical Properties of Wood-Polymer Hybrid Composites Prepared by Injection Molding. **Polymers**, v. 13, p. 2849, 2021. DOI: <<https://doi.org/10.3390/polym13172849>>.

[101] SHULGA, G.; NEIBERTE, B. Aminated wood sanding dust as filler for recycled polypropylene-based composite. **Cellulose Chem. Technol.**, v. 53, p. 945–953, 2019. DOI: <<https://dx.doi.org/10.35812/CelluloseChemTechnol.2019.53.92>>.

[102] PATEL, V.K.; RAWAT, N. Physico-mechanical properties of sustainable Sagwan-Teak Wood Flour/Polyester Composites with/without gum rosin. **Sustainable Materials and Technologies**, v. 13, p. 1–8, 2017. DOI: <<https://dx.doi.org/10.1016/j.susmat.2017.05.002>>.

[103] KHAN, M.Z.; SRIVASTAVA, S.K.; GUPTA, M. Enhancement of the properties of hybrid woods polymer composites by chemical pre-treatments. Proceedings of the Institution of Mechanical Engineers, Part L: Journal of Materials: Design and Applications, v. 235, p. 828–841, 2021. DOI: <<https://doi.org/10.1177/1464420720980033>>.

[104] SOUISSI, S.; LACHTAR, F.; ELLOUMI, A.; BERGERET, A. Properties of wood polymer composites based on polypropylene/olive wood flour: effects of fiber treatment and compatibilizer. **Iranian Polymer Journal**, [s.l.], v. 31, n. 12, p. 1511–1521, 2022. DOI: <<https://doi.org/10.1007/s13726-022-01089-x>>.

[105] TOMCZAK, D.; WOŹNIAK, M.; RATAJCZAK, I.; SIP, A.; BARANOWSKA, M.; BULA, K.; ČABALOVÁ, I.; BUBÉNIKOVÁ, T.; BORYSIK, S. Caffeine-treated wood as an innovative filler for advanced polymer composites. **Journal of Wood Chemistry and Technology**, [s.l.], v. 43, n. 5, p. 271–288, 2023. DOI: <<https://doi.org/10.1080/02773813.2023.2237498>>.

- [106] PHUNG, A. T.; DZUNG, H. T.; LINH, N. P. D.; DUC, V. M.; LIEM, N. T. Acrylonitrile butadiene styrene/ wood sawdust particles composites: mechanical and morphological properties. **Iranian Polymer Journal**, [s.l.], v. 33, n. 1, p. 67–78, 2024. DOI: <<https://doi.org/10.1007/s13726-023-01236-y>>.
- [107] KLYOSOV, A.A. Wood-Plastic Composites. **New Jersey: John Wiley & Sons**, 2007.
- [108] WANG, Y. **Morphological Characterization of Wood Plastic Composite (WPC) with Advanced Imaging Tools: Developing Methodologies for Reliable Phase and Internal Damage Characterization**. 2007. Available at: <https://ir.library.oregonstate.edu/concern/graduate_thesis_or_dissertations/mc87ps55z>.
- [109] RAGAERT, K.; DELVA, L.; VAN GEEM, K. Mechanical and chemical recycling of solid plastic waste. **Waste Management**, v. 69, p. 24–58, 2017. DOI: <<https://doi.org/10.1016/j.wasman.2017.07.044>>.
- [110] MANDAL, M.; BARDHAN, P.; MAJI, T.K. Development of wood polymer composites with thermosetting resin from soybean oil cross-linked with rosin derivative. **Eur. J. Wood Prod.**, v. 78, p. 1265–1278, 2020. DOI: <<https://doi.org/10.1007/s00107-020-01564-3>>.
- [111] GIRDIS, J. et al. Rethinking Timber: Investigation into the Use of Waste Macadamia Nut Shells for Additive Manufacturing. **JOM**, v. 69, p. 575–579, 2017. DOI: <<https://doi.org/10.1007/s11837-016-2213-6>>.
- [112] HOMKHIEW, C.; RAWANGWONG, S.; BOONCHOUYTAN, W.; SUCHAIYA, V. Morphological, mechanical, and physical properties of ground rubber tire thermoplastic elastomer/rubberwood sawdust composites: effects of composition contents and rubber types. **Journal of Thermoplastic Composite Materials**, [s.l.], v. 36, n. 5, p. 1952–1977, 2023. DOI: <<https://doi.org/10.1177/08927057221086834>>.
- [113] BÜTÜN, F.Y. et al. The effect of fibreboard (MDF) disintegration technique on wood polymer composites (WPC) produced with recovered wood particles. **Composites Part A: Applied Science and Manufacturing**, v. 118, p. 312–316, 2019. DOI: <<https://doi.org/10.1016/j.compositesa.2019.01.006>>.
- [114] KALE, A. et al. Lantana Fiber-Filled Polypropylene Composite. In: PANDEY, K. et al. (eds). **Wood is Good**. Singapore: Springer, 2017. p. 1–480. DOI: <https://doi.org/10.1007/978-981-10-3115-1_31>.
- [115] MAZZANTI, V.; MOLLICA, F. Bending Properties of Wood Flour Filled Polyethylene in Wet Environment. **Procedia Engineering**, v. 200, p. 68–72, 2017. DOI: <<https://doi.org/10.1016/j.proeng.2017.07.011>>.
- [116] FORTINI, A.; MAZZANTI, V. Combined effect of water uptake and temperature on wood polymer composites. **Journal of Applied Polymer Science**, v. 135, 2018. DOI: <<https://doi.org/10.1002/app.46674>>.
- [117] KRYVOLAPOV, D. S.; SUKHYY, K. M.; BASHTANYK, P. I.; TRETYAKOV, A. O.; BEZRUKAVY, V. A. Influence of stearic acid on the properties of wood-polymer composites. **Voprosy Khimii i Khimicheskoi Tekhnologii**, [s.l.], v. 150, n. 5, p. 50–54, 2023. DOI: <<https://doi.org/10.32434/0321-4095-2023-150-5-50-54>>.
- [118] DUAN, G.; HE, C.; WANG, M.; YANG, X.; WANG, W.; WANG, Y. Effect of silica on thermal and mechanical properties of eucalyptus-PVC wood-polymer composites. **BioResources**, [s.l.], v. 18, n. 1, p. 1803–1811, 2023. DOI: <<https://doi.org/10.15376/biores.18.1.1803-1811>>.
- [119] ZHANG, J.; KOU BAA, A.; XING, D.; WANG, H.; TAO, Y.; WANG, X. M.; LI, P. Fire behavior and failure model of multilayered wood flour/HDPE/polycarbonate composites with a sandwich structure. **Polymers, Basel**, v. 14, n. 14, p. 2833, 2022. DOI: <<https://doi.org/10.3390/polym14142833>>.
- [120] HAO, X. et al. Interfacial adhesion mechanisms of ultra-highly filled wood fiber/polyethylene composites using maleic anhydride grafted polyethylene as a compatibilizer. **Materials & Design**, v. 212, p. 110182, 2021. DOI: <<https://doi.org/10.1016/j.matdes.2021.110182>>.
- [121] MOSIA, L.; PHIRI, M. J.; GARDE, K.; HLANGOTHI, S. P. Effect of ethylene-1-butene as a compatibilizer for the optimization of wood flour and ground tyre rubber in polypropylene composites. **Journal of Composites Science, Basel**, v. 6, n. 8, p. 220, 2022. DOI: <<https://doi.org/10.3390/jcs6080220>>.

[122] LOURENÇON, T.V.; SANTILLI, B.V.; MAGALHÃES, W.L.E.; MUNIZ, G.I.B. Thermal Stabilization of Wood/ Polypropylene Composites Through Addition of Unmodified, Low-Cost Kraft Lignin. **Waste Biomass Valorization**, v. 11, p. 1555–1563, 2020. DOI: <<https://doi.org/10.1007/s12649-018-0484-6>>.

[123] ADEBAYO, G.O.; HASSAN, A.; YAHYA, R.; RAHMAN, N.A.; LAFIA-ARAGA, R. Influence of wood surface chemistry on the tensile and flexural properties of heat-treated mangrove/high-density polyethylene composites. **Polymer Bulletin**, v. 76, p. 6467–6486, 2019. DOI: <<https://doi.org/10.1007/s00289-019-02731-0>>.

[124] MAZZANTI, V.; CAVALCOLI, V.; BALBO, A.; MOLICA, F. Hygrothermal degradation effects on a rubber toughened WPC. **Materials Today: Proceedings**, v. 31, p. S209–S212, 2020. DOI: <<https://doi.org/10.1016/j.matpr.2019.11.062>>.

[125] HARTMANN, R.; KOCH, M. Wood chip plastic composite – a novel bio-based material with high mechanical properties. **Polimery**, v. 62, p. 556–559, 2017. DOI: <<https://doi.org/10.14314/polimery.2017.556>>.

[126] MAKVANDI, P.; IFTEKHAR, S.; PIZZETTI, F.; ZAREPOUR, A.; ZARE, E.; ASHRAFIZADEH, M.; AGARWAL, T.; PADIL, V.; MOHAMMADINEJAD, R.; SILLANPAA, M.; MAITI, T.; PERALE, G.; ZARRABI, A.; ROSSI, F. Functionalization of polymers and nanomaterials for water treatment, food packaging, textile and biomedical applications: a review. **Environmental Chemistry Letters**, [s.l.], v. 19, p. 583–611, 2020. DOI: <<https://doi.org/10.1007/s10311-020-01089-4>>.

[127] DELFI, M.; GHOMI, M.; ZARRABI, A.; MOHAMMADINEJAD, R.; TARAGHDARI, Z.; ASHRAFIZADEH, M.; ZARE, E.; AGARWAL, T.; PADIL, V.; MOKHTARI, B.; ROSSI, F.; PERALE, G.; SILLANPAA, M.; BORZACCHIELLO, A.; MAITI, T.; MAKVANDI, P. Functionalization of polymers and nanomaterials for biomedical applications: antimicrobial platforms and drug carriers. **Prosthesis**, [s.l.], 2020. DOI: <<https://doi.org/10.3390/prosthesis2020012>>.

[128] BOOTH, J.; MOZETIČ, M.; NIKIFOROV, A.; OEHR, C. Foundations of plasma surface functionalization of polymers for industrial and biological applications.

Plasma Sources Science and Technology, [s.l.], v. 31, 2022. DOI: <<https://doi.org/10.1088/1361-6595/ac70f9>>.

[129] WANG, S.; CHEN, K.; JIA, M.; XUE, P. Effect of processing conditions on the microstructure of microcellular PP/WF composites prepared by the continuous extrusion molding technology. **Materials Research Express**, v. 7, 2020. DOI: <<https://doi.org/10.1088/2053-1591/ab5d73>>.

[130] BÜTÜN, F.Y.; MAYER, A.K.; OSTENDORF, K.; GRÖNE, O.-E.Z.; KRAUSE, K.C.; SCHÖPPER, C.; MERTENS, O.; KRAUSE, A.; MAI, C. Recovering fibres from fibreboards for wood polymer composites production. **International Wood Products Journal**, v. 9, p. 42–49, 2018. DOI: <<https://doi.org/10.1080/20426445.2018.1462965>>.

[131] PRAPRUDDIVONGS, C.; SOMBATSOMPOP, N. Wood, silver-substituted zeolite and triclosan as biodegradation controllers and antibacterial agents for poly(lactic acid) (PLA) and PLA composites. **Journal of Thermoplastic Composite Materials**, v. 30, p. 583–598, 2017. DOI: <<https://doi.org/10.1177/0892705715604683>>.

[132] TUNCEV, D.V.; SATTAROVA, Z.G.; GALIEV, I.M. Multi-Layer Wood-Polymer Composite. **Solid State Phenomena**, v. 265, p. 47–52, 2017. DOI: <<https://doi.org/10.4028/www.scientific.net/SSP.265.47>>.

[133] KHANTIMIROV, A. G.; ABDRAKHMANOVA, L. A.; NIZAMOV, R.K.; KHOZIN, V.G. Investigation of properties in nanomodified polyethylene-based wood-polymer composites. **Nanotekhnologii v Stroitel'stve**, [s.l.], v. 15, n. 2, p. 110–116, 2023. DOI: <<https://doi.org/10.15828/2075-8545-2023-15-2-110-116>>.

[134] LEWANDOWSKI, K.; PISZCZEK, K.; SKÓRCZEWSKA, K.; MIROWSKI, J.; ZAJCHOWSKI, S.; WILCZEWSKI, S. Rheological properties of wood polymer composites at high shear rates – Evaluation of additional pressure losses as a result of inlet effects. **Composites Part A: Applied Science and Manufacturing**, v. 154, p. 106804, 2022. DOI: <<https://doi.org/10.1016/j.compositesa.2022.106804>>.

[135] MANDAL, M.; BORGOHAIN, P.; BEGUM, P.; DEKAA, R.C.; MAJI, T.K. Property enhancement and DFT study

of wood polymer composites using rosin derivatives as co-monomers. **New Journal of Chemistry**, v. 42, p. 2260–2269, 2018. DOI: <<https://doi.org/10.1039/C7NJ03825A>>.

[136] NUKALA, S. G.; KONG, I.; KAKARLA, A. B.; TSHAI, K. Y.; KONG, W. Preparation and characterisation of wood polymer composites using sustainable raw materials. **Polymers**, v. 14, n. 15, p. 3183, 2022. DOI: <<https://doi.org/10.3390/polym14153183>>.

[137] LAZRAK, C.; KABOUCHI, B.; HAMMI, M.; FAMIRI, A.; ZIANI, M. Structural study of maritime pine wood and recycled high-density polyethylene (HDPEr) plastic composite using Infrared-ATR spectroscopy, X-ray diffraction, SEM and contact angle measurements. **Case Studies in Construction Materials**, v. 10, 2019. DOI: <<https://doi.org/10.1016/j.cscm.2019.e00227>>.

[138] MANDAL, M.; MAJI, T.K. Comparative study on the properties of wood polymer composites based on different modified soybean oils. **Journal of Wood Chemistry and Technology**, v. 37, p. 124–135, 2017. DOI: <<https://doi.org/10.1080/02773813.2016.1253099>>.

[139] HEJNA, A.; KOSMELA, P. Insights into Compatibilization of Poly(ε-caprolactone)-based Biocomposites with Diisocyanates as Modifiers of Cellulose Fillers. **Malayan Journal of Science and Technology**, v. 18, p. 221–241, 2020.

[140] MIRSKI, R.; DZIURKA, D.; BANASZAK, A. Using rape particles in the production of polymer and lignocellulose boards. **BioResources**, v. 14, p. 6736–6746, 2019.

[141] MANDAL, M.; NATH, D.; MAJI, T.K. Wood polymer nanocomposites from functionalized soybean oil and nanoclay. **Wood Science and Technology**, v. 52, p. 1621–1643, 2018. DOI: <<https://doi.org/10.1007/s00226-018-1043-9>>.

[142] HUANG, Y. et al. A branched polyelectrolyte complex enables efficient flame retardant and excellent robustness for wood/polymer composites. **Polymers**, v. 12, p. 2438, 2020. DOI: <<https://doi.org/10.3390/polym12112438>>.

[143] NUKALA, S. G.; KONG, I.; KAKARLA, A. B.; KONG, W.; KONG, W. Development of wood polymer composites from recycled wood and plastic waste: thermal and mechanical properties. **Journal of Composites Science**, v. 6, n. 7, p. 194, 2022. DOI: <<https://doi.org/10.3390/jcs6070194>>.

[144] FRAĆCZ, W.; JANOWSKI, G. Determination of viscosity curve and pvt properties for wood-polymer composite. **Wood Research**, v. 63, p. 321–334, 2018.

[145] RATHOD, Y.; BARI, P.; HANSORA, D.P.; MISHRA, S. Elaboration of performance of tea dust–polypropylene composites. **Journal of Applied Polymer Science**, v. 134, 2017. DOI: <<https://doi.org/10.1002/app.44750>>.

[146] SIWEK, S.; OKTAE, J.; GRASSETT-GILLE, S.; WAGENFÜHR, A. Influence of different wood flour fractions on the mechanical properties of injection molded WPC with cellulose propionate. **European Journal of Wood Production**, v. 76, p. 499–507, 2018. DOI: <<https://doi.org/10.1007/s00107-017-1265-9>>.

[147] CHAN-HOM, T.; YAMSAENG SUNG, W.; PRAPAGDEE, B.; MARKPIN, T.; SOMBATSOMPOP, N. Flame retardancy, antifungal efficacies, and physical–mechanical properties for wood/polymer composites containing zinc borate. **Fire and Materials**, v. 41, p. 675–687, 2017. DOI: <<https://doi.org/10.1002/fam.2408>>.

[148] FRAĆCZ, W.; JANOWSKI, G.; BAŁ, Ł. The possibilities of using poly (3-hydroxybutyrate-co-3-hydroxyvalerate) PHBV in the production of wood–polymer composites. **Journal of Composites Science**, v. 7, n. 12, p. 509, 2023. DOI: <<https://doi.org/10.3390/jcs7120509>>.

[149] KRUSZELNICKA, I.; GINTER-KRAMARCZYK, D.; MUSZYŃSKI, P. Influence of surfactants used in the paper industry on polymer-wood composites under static test conditions. **Desalination and Water Treatment**, v. 268, p. 146–152, 2022. DOI: <<https://doi.org/10.5004/dwt.2022.28665>>.

[150] BEK, M.; AULOVA, A.; ČREŠNAR, K. P.; MATKOVIČ, S.; KALIN, M.; PERŠE, L. S. Long-term creep compliance of wood polymer composites: using untreated wood fibers as a filler in recycled and neat polypropylene matrix. **Polymers**, v. 14, n. 13, p. 2539, 2022. DOI: <<https://doi.org/10.3390/polym14132539>>.

[151] SOZEN, E.; AYDEMIR, D.; ZOR, M. The effects of lignocellulosic fillers on mechanical, morphological and thermal properties of wood polymer composites. **Drvna Industrija**, v. 68, p. 195–204, 2017. DOI: <<https://doi.org/10.5552/drind.2017.1709>>.

[152] CHITRA, K.N. et al. Characterization of wood polymer composite and design of root trainer. In: Proceedings of the International Conference on Emerging Trends in Science, Technology and Management, Karnataka, India, 2018. p. 020126. DOI: <<http://dx.doi.org/10.1063/1.5029702>>.

[153] ARUN, A.K. et al. Fabrication and testing of novel hybrid carbon composite for aircraft applications. **ACS Journal of Science and Engineering**, v. 2, p. 33–40, 2022. DOI: <<https://doi.org/10.34293/acsjse.v2i1.26>>.

[154] NAGAMADHU, M.; KUMAR, G.C.M.; JEYARAJ, P. Effect of stacking sequence on mechanical properties of neem wood veneer plastic composites. In: Proceedings of the International Conference on Emerging Trends in Science, Technology and Management, Karnataka, India, 2018. p. 020029. DOI: <<https://doi.org/10.1063/1.5029605>>.

[155] JAWAID, M.; THARIQ, M. Sustainable composites for aerospace applications. **Woodhead Publishing**, 2018.

[156] KHAN, M.Z.R.; SRIVASTAVA, S.K.; GUPTA, M.K. A state-of-the-art review on particulate wood polymer composites: Processing, properties and applications. **Polymer Testing**, v. 89, p. 106721, 2020. DOI: <<https://doi.org/10.1016/j.polymertesting.2020.106721>>.

[157] LIU, T. et al. Selective cleavage of ester linkages of anhydride-cured epoxy using a benign method and reuse of the decomposed polymer in new epoxy preparation. **Green Chemistry**, v. 19, p. 4364–4372, 2017. DOI: <<https://doi.org/10.1039/C7GC01737E>>.

[158] BALAGA, U.K. et al. Characterization and comparison of thin ply IM7/8552 composites processed by automated tape placement and hand layup. **Journal of Composite Materials**, v. 57, p. 2243–2260, 2023. DOI: <<https://doi.org/10.1177/00219983231168943>>.

[159] MIELES, M.; STITT, C.; JI, H. F. Bulk polymerization of PEGDA in spruce wood using a DBD plasma-initiated

process to improve the flexural strength of the wood-polymer composite. **Plasma**, v. 5, n. 1, p. 146–153, 2022. DOI: <<https://doi.org/10.3390/plasma5010011>>.

[160] JIANG, Y.; ZHANG, M.; WENG, M.; LIU, X.; RONG, X.; HUANG, Q.; WANG, L. Hemicellulose-rich transparent wood: microstructure and macroscopic properties. **Carbohydrate Polymers**, v. 296, p. 119925, 2022. DOI: <<https://doi.org/10.1016/j.carbpol.2022.119925>>.

[161] YANG, T.; ZHONG, H.; XU, C.; LUO, D.; MEI, C. Fabrication and mechanism analysis of wood polymer composites with improved hydrophobicity, dimensional stability and mechanical strength. **Cellulose**, v. 30, n. 5, p. 3099–3112, 2023. DOI: <<https://doi.org/10.1007/s10570-023-05056-4>>.

[162] MARTINS, C. I.; GIL, V.; ROCHA, S. Thermal, mechanical, morphological and aesthetical properties of rotational molding PE/pine wood sawdust composites. **Polymers**, v. 14, n. 1, p. 193, 2022. DOI: <<https://doi.org/10.3390/polym14010193>>.

[163] MOHAMMED, A.S.; MEINCKEN, M. Properties of low-cost WPCs made from alien invasive trees and rLDPE for interior use in social housing. **Polymers**, v. 13, p. 2436, 2021. DOI: <<https://doi.org/10.3390/polym13152436>>.

[164] WANG, S. et al. Research on the preparation and properties of foamed PP/wood flour composites. **Materials Research Express**, v. 7, p. 035308, 2020. DOI: <<https://doi.org/10.1088/2053-1591/ab802e>>.

[165] GE, S.; SHI, Y.; CHEN, X.; ZHOU, Y.; NAUSHAD, M.; VERMA, M.; ...; PENG, W. Sustainable upcycling of plastic waste and wood fibers into high-performance laminated wood-polymer composite via one-step cell collapse and chemical bonding approach. **Advanced Composites and Hybrid Materials**, v. 6, n. 4, p. 146, 2023. DOI: <<https://doi.org/10.1007/s42114-023-00723-3>>.

[166] YILMAZ ATAY, H.; TÜRKMEN, M. Use of hornbeam, pine and MDF waste in wood-polymer composites as construction elements. **Journal of the Indian Academy of Wood Science**, v. 19, n. 2, p. 110–120, 2022. Available at: <<https://doi.org/10.1007/s13196-022-00303-w>>.

- [167] LUBIS, A.M.H.S. et al. Mechanical properties of oil palm frond wood filled thermoplastic polyurethane. **International Journal of Nanoelectronics and Materials**, v. 13, p. 255–266, 2020.
- [168] KOYUNCU, M. Experimental investigation of epoxy matrix and pine sawdust reinforced wood-polymer composite materials. *BioResources*, v. 17, n. 1, p. 1161-1172, 2022. Available at: <<https://doi.org/10.15376/biores.17.1.1161-1172>>.
- [169] SABA, K.; RANA, A.K.; JAYAKRISHNA, K.; RAHMAN, M.M. A review on mechanical and physical properties of natural fiber reinforced polymer composites. **Composites Part B: Engineering**, v. 106, p. 147–166, 2017. DOI: <<https://doi.org/10.1016/j.compositesb.2011.01.010>>.
- [170] CLEMONS, I. Effects of processing method and moisture history on laboratory fungal resistance of wood-HDPE composites. **Forest Products Journal**, v. 54, p. 50–57, 2004.
- [171] LAZRAC, C.; HAMMI, M. Experimental and modeling studies on water absorption kinetics of recycled wood-polymer composites. **Journal of the Indian Academy of Wood Science**, v. 19, n. 2, p. 52–60, 2022. Available at: <<https://doi.org/10.1007/s13196-022-00302-x>>.
- [172] ANDRZEJEWSKI, J.; BARCZEWSKI, M.; SZOSTAK, M. Injection molding of highly filled polypropylene-based biocomposites. Buckwheat husk and wood flour filler: A comparison of agricultural and wood industry waste utilization. **Polymers**, v. 11, 2019. DOI: <<https://doi.org/10.3390/polym11111881>>.
- [173] LELUK, K.; FRĄCKOWIAK, S.; LUDWICZAK, J.; RYDZKOWSKI, T.; THAKUR, V. The impact of filler geometry on polylactic acid-based sustainable polymer composites. **Molecules**, v. 26, 2020. DOI: <<https://doi.org/10.3390/molecules26010149>>.
- [174] KUMAR, V. et al. Effect of gamma irradiation on tensile and thermal properties of poplar wood flour-linear low density polyethylene composites. **Radiation Physics and Chemistry**, v. 174, p. 108922, 2020. DOI: <<https://doi.org/10.1016/j.radphyschem.2020.108922>>.
- [175] LAZRAC, C.; KIFANI-SAHBAN, F.; HAMMI, M.; ZIAT, Y. Effect studies of recycled polymer and CaCO₃ on the moisture resistance of processed wood–polymer composites. **Journal of the Indian Academy of Wood Science**, v. 20, n. 2, p. 107–116, 2023. DOI: <<https://doi.org/10.1007/s13196-023-00314-1>>.
- [176] YOUNESI-KORDKHEILI, H.; PIZZI, A. Nanolignin, a coupling bio-agent for wood-plastic composites. **Journal of Renewable Materials**, v. 11, n. 5, p. 2075–2083, 2023. DOI: <<https://doi.org/10.32604/jrm.2023.026706>>.
- [177] ASTM. D7032-21: Standard Specification for Establishing Performance Ratings for Wood-Plastic Composite and Plastic Lumber Deck Boards, Stair Treads, Guards, and Handrails. **West Conshohocken: ASTM International**, 2021.
- [178] ASTM. D7264/D7264M-21: Standard Test Method for Flexural Properties of Polymer Matrix Composite Materials. **West Conshohocken: ASTM International**, 2021.
- [179] ASTM. D790-17: Standard Test Methods for Flexural Properties of Unreinforced and Reinforced Plastics and Electrical Insulating Materials. **West Conshohocken: ASTM International**, 2017.
- [180] ASTM. D638-14: Standard Test Method for Tensile Properties of Plastics. **West Conshohocken: ASTM International**, 2022.
- [181] ISO 20819-1. Plastics - Wood-plastic recycled composites (WPRC) - Part 1: Specification. **Geneva: International Organization for Standardization**, 2020.

ACKNOWLEDGEMENT

We sincerely acknowledge the agencies CNPq (National Council for Scientific and Technological Development - Undergraduate Research Grant PIBITI 06/2021 from Tiago Vieira da Silva), CAPES (Coordination for the Improvement of Higher Education Personnel - Financial Code 001 - master's scholarship from Anderson Ravik dos Santos and Rivelino Neri Silva) and PROPPI/UFOP (Pro-Rectorate of Research and Innovation of the Federal University of Ouro Preto, for Research Grant 25/2022 granted to Wanna Carvalho Fontes). We are also

grateful for the collaboration of the EcoUrb Research and Extension Group – CNPq.

AUTHORS

ORCID: [0000-0001-5047-7630](https://orcid.org/0000-0001-5047-7630)

ANDERSON RAVIK DOS SANTOS | Mestre | Universidade Federal de Ouro Preto | Engenharia Civil | Ouro Preto, MG | Correspondência para: Universidade Federal de Ouro Preto (UFOP). Campus Morro do Cruzeiro, Bauxita, Ouro Preto – MG, CEP: 35.400-000.
e-mail: anderson.ravik@aluno.ufop.edu.br

ORCID: [0009-0008-5410-5875](https://orcid.org/0009-0008-5410-5875)

TIAGO VIEIRA DA SILVA | Graduação | Universidade Federal de Ouro Preto | Engenharia Urbana | Ouro Preto, MG | Correspondência para: Universidade Federal de Ouro Preto (UFOP). Campus Morro do Cruzeiro, Bauxita, Ouro Preto – MG, CEP: 35.400-000.
e-mail: tiago.vs@aluno.ufop.edu.br

ORCID: [0009-0008-8196-6443](https://orcid.org/0009-0008-8196-6443)

ROMÁRIO PARREIRA PITA | Mestre | Universidade Federal de Ouro Preto | Engenharia Civil | Ouro Preto, MG | Correspondência para: Universidade Federal de Ouro Preto (UFOP). Campus Morro do Cruzeiro, Bauxita, Ouro Preto – MG, CEP: 35.400-000.
e-mail: romario.pita@aluno.ufop.edu.br

ORCID: [0000-0001-9383-137X](https://orcid.org/0000-0001-9383-137X)

RIVELINO NERI SILVA | Mestre | Universidade Federal de Ouro Preto | Engenharia Civil | Ouro Preto, MG | Correspondência para: Universidade Federal de Ouro Preto (UFOP). Campus Morro do Cruzeiro, Bauxita, Ouro Preto – MG, CEP: 35.400-000.
e-mail: rivelino.silva@aluno.ufop.edu.br

ORCID: [0000-0001-5253-2891](https://orcid.org/0000-0001-5253-2891)

WANNA CARVALHO FONTES | Doutora | Universidade Federal de Ouro Preto | Engenharia Civil | Ouro Preto, MG | Correspondência para: Universidade Federal de Ouro Preto (UFOP). Campus Morro do Cruzeiro, Bauxita, Ouro Preto – MG, CEP: 35.400-000.
e-mail: wanna.fontes@ufop.edu.br

HOW TO CITE THIS ARTICLE:

SANTOS, A. R.; SILVA, T. V.; PITA, R. P.; SILVA, R. N.; FONTES, W. C. Exploring Wood Polymer Composites: A Systematic Visual Review of Composition, Production, and Properties. **MIX Sustentável**, v.11, n.2, p.139-164. ISSN 2447-3073. Disponível em: <<http://www.nexos.ufsc.br/index.php/mixsustentavel>>. Acesso em: _/_/_.

SUBMITTED ON: 15/10/2024

ACCEPTED ON: 08/09/2025

PUBLISHED ON: 01/10/2025

RESPONSIBLE EDITORS: Lisiane Ilha Librelotto e Paulo Cesar Machado Ferroli

Record of authorship contribution:

CRedit Taxonomy (<http://credit.niso.org/>)

ARS: conceptualization, methodology, investigation, data curation and project administration.

TVS: conceptualization, formal analysis, investigation and data curation.

RPP: data curation and writing - original draft.

RNS: data curation and writing - original draft.

WCF: supervision and writing- reviewing & editing

Conflict declaration: nothing to declare.